



Heriot-Watt University
Research Gateway

Vector Vortex Beam Generation with a Single Plasmonic Metasurface

Citation for published version:

Yue, F, Wen, D, Xin, J, Gerardot, BD, Li, J & Chen, X 2016, 'Vector Vortex Beam Generation with a Single Plasmonic Metasurface', *ACS Photonics*, vol. 3, no. 9, pp. 1558-1563.
<https://doi.org/10.1021/acsp Photonics.6b00392>

Digital Object Identifier (DOI):

[10.1021/acsp Photonics.6b00392](https://doi.org/10.1021/acsp Photonics.6b00392)

Link:

[Link to publication record in Heriot-Watt Research Portal](#)

Document Version:

Peer reviewed version

Published In:

ACS Photonics

Publisher Rights Statement:

This document is the unedited author's version of a Submitted Work that was subsequently accepted for publication in ACS Photonics, © American Chemical Society after peer review. To access the final edited and published work, see <http://pubs.acs.org/doi/abs/10.1021/acsp Photonics.6b00392>

General rights

Copyright for the publications made accessible via Heriot-Watt Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

Heriot-Watt University has made every reasonable effort to ensure that the content in Heriot-Watt Research Portal complies with UK legislation. If you believe that the public display of this file breaches copyright please contact open.access@hw.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.

Vector Vortex Beam Generation with a Single Plasmonic Metasurface

Fuyong Yue, Dandan Wen, Jingtao Xin, Brian D. Gerardot, Jensen Li, and Xianzhong Chen

ACS Photonics, **Just Accepted Manuscript** • DOI: 10.1021/acsp Photonics.6b00392 • Publication Date (Web): 20 Jul 2016

Downloaded from <http://pubs.acs.org> on July 20, 2016

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

Vector Vortex Beam Generation with a Single Plasmonic Metasurface

Fuyong Yue¹, Dandan Wen¹, Jingtao Xin², Brian D. Gerardot¹, Jensen Li³, Xianzhong Chen^{1*}

1. SUPA, Institute of Photonics and Quantum Sciences, School of Engineering and Physical Sciences,

Heriot-Watt University, Edinburgh, EH14 4AS, UK

2. Beijing Engineering Research Centre of Optoelectronic Information and Instruments, Beijing Information Science and Technology University, Beijing, 100192, China

3. School of Physics and Astronomy, University of Birmingham, B15 2TT

Abstract: Despite a plethora of applications ranging from quantum memories to high-resolution lithography, the current technologies to generate vector vortex beams (VVBs) suffer from less efficient energy use poor resolution, low damage threshold, and bulky size, preventing further practical applications. We propose and experimentally demonstrate an approach to generate VVBs with a single metasurface by locally tailoring phase and transverse polarization distribution. This method features the spin-orbit coupling and the superposition of the converted part with an additional phase pickup and the residual part without a phase change. By maintaining the equal components for the converted part and the residual part, the cylindrically polarized vortex beams carrying orbital angular momentum are experimentally demonstrated based on a single metasurface at subwavelength scale. The proposed approach provides unprecedented freedom in engineering the properties of optical waves with the high-efficiency light utilization and a minimal footprint.

Key words: metasurface, vector vortex beam, orbital angular momentum, inhomogeneous polarization distribution

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
Structured beams such as vortex beams (VBs) and vector vortex beams (VVBs) have been widely investigated as new promising resources due to the extra degree of freedom for light manipulation. VBs have a distribution of azimuthal phase and homogeneous polarization, while VVBs have inhomogeneous polarization distribution (such as radial polarization) in the transverse plane and also carry orbital angular momentum. The applications of structured beams have been found in quantum memories¹, particle trapping², optical communication³⁻⁴, as well as high-resolution lithography⁵⁻⁸. A radially polarized beam, for example, can be focused more sharply and give rise to a centred longitudinal field, paving the way to higher-resolution lithography and optical sensing. An azimuthally polarized beam with a helical phase front, which carries an orbital angular momentum, can effectively achieve a significantly smaller spot size in comparison with that for a radially polarized beam with a planar wavefront in a higher-NA condition. Many approaches and methods, including liquid crystal q-plates⁹⁻¹⁰, spatial light modulator and optical elements using femtosecond laser direct writing technology¹¹, have been proposed to generate vector vortex beams. However, these systems could not be straightforwardly downsized, preventing from widespread applications in integrated optics. In addition, the limitations of poor resolution, low damage threshold still need to be overcome for practical applications. There are numerous challenges, either fundamental or technological, in building devices that are compact, efficient and integrable.

38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
Optical metasurfaces, ultrathin inhomogeneous media with planar structures of nanopatterns that manipulate the optical properties of light at the subwavelength scale, have become a current subject of intense research due to the unprecedented control of light propagation. Metasurfaces have been widely used in many exotic research areas, including photonic spin Hall effect¹², invisibility cloaking¹³, lensing¹⁴⁻¹⁸, and holography¹⁹⁻²⁰. Specially, geometric metasurface, regarded functionally as Pancharatnam-Berry phase optical elements²¹⁻²², is one of the most exciting recent advances in nano-optics due to their capability of tailoring the field of the emerging beams into nontrivial structures based on optical spin-orbit interaction²³⁻²⁴. Geometric metasurfaces have been reported to realize orbital angular momentum generation²⁵⁻²⁸. However, the conversion efficiency is limited and only the converted part with an additional phase pickup is used. Consequently, various methods to

1
2
3 improve the conversion efficiency of plasmonic metasurface are investigated, such as
4 catenary metasurface²⁹⁻³⁰, hybrid bilayer metasurface³¹, planarized metasurface stack³²,
5
6 monolayer reflective metasurface and so on. Nevertheless, the polarization distribution of the
7 beam is still homogeneous since all the functionalities are limited to the phase control.
8
9 Although one possible solution is to employ two cascaded metasurfaces³³ to generate
10 structured beam of vector vortex, the complexity of the required optical system and its large
11 volume sharply affect its performance in system integration and competition capability.
12
13 Therefore, considering the effective generation of VVBs, an ideal solution is to use a single
14 metasurface to generate these beams carrying an orbital angular momentum with an
15 inhomogeneous polarization distribution.
16
17
18
19
20
21
22

23 In this work, we propose and experimentally demonstrate an approach to generate VVBs
24 using a single reflective-type metasurface. The VVBs are generated by using the
25 superposition of the converted part and the residual part of the output beam. The designed
26 metasurfaces to generate cylindrical VVBs carrying orbital angular momentum (OAM) are
27 experimentally demonstrated and characterized. To further validate our proposed approach, a
28 phase-gradient metasurface (PGM) is adopted as a circular polarization beam splitter to
29 decompose the resultant beam. The proposed method opens a new window to generate VVBs
30 using a single metasurface, providing new capabilities to develop novel compact devices that
31 may lead to advances in a wide range of fields in optics and photonics.
32
33
34
35
36
37
38
39

40 **DESIGN OF THE METASURFACE**

41
42
43 Figure 1 shows the schematic of vector vortex beam generation. For an incident light beam,
44 the reflected light from the metasurface consists of two circular polarization states: one has
45 the same handedness as the incident circularly polarized light but with an additional phase
46 delay³⁴ and the other has the opposite handedness without the additional phase delay. The
47 additional phase delay is known as Pancharatnam–Berry phase with a value of $\pm 2\varphi$, where φ
48 is the orientation angle of each nanorod. Specifically, “+” and “-” represent the sign of the
49 phase shift for the incident RCP light and that for the incident LCP light, respectively. Note
50 that the helicity of polarized light is reversed when it is reflected by an ideal mirror because of
51 the opposite propagation direction. Each pixel size is subwavelength scale. The output beam
52
53
54
55
56
57
58
59
60

is therefore a superposition of two components, and thus the polarization distribution is engineered at nanoscale and transformed to a radial vector field. Upon the illumination of (right-handed circularly polarized) RCP light, the generated VVB has a helical wavefront and carries OAM $\ell = 1$. Furthermore, the polarization distribution is flipped about the vertical axis (see Supplementary Section 1) and the sign of OAM is reversed when changing the polarization of incident light from RCP to left-handed circular polarization (LCP).

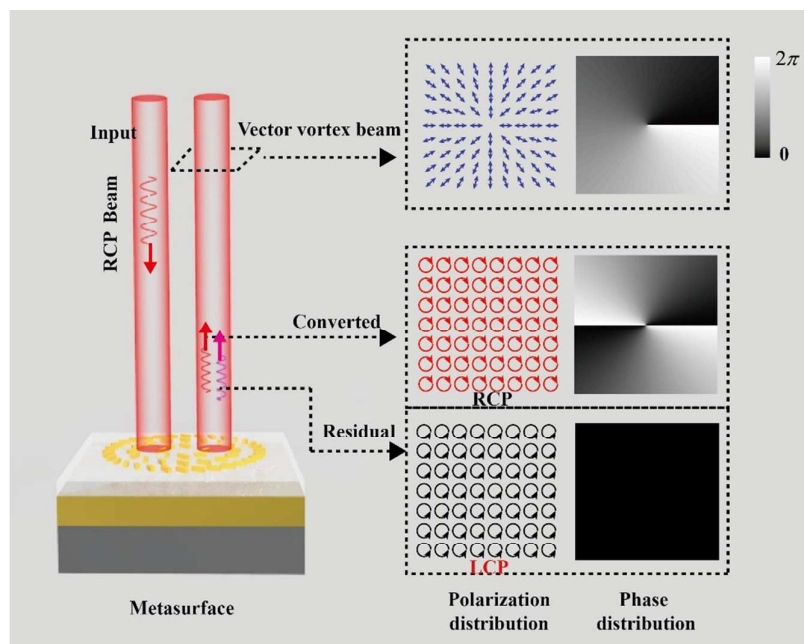


Figure 1. Schematic of the vector vortex beam generation through a metasurface, and the polarization and phase distributions of the generated beams. The resultant beam is a superposition of the converted part and the residual part. The converted part has the same circular polarization as that of the incident beam and an additional phase pickup, while the residual part has opposite helicity but no phase change. Upon the illumination of RCP light, the converted beam has a helical wavefront with a topological charge of $\ell = 2$ and the resultant beam has radial polarization distribution with the OAM of $\ell = 1$. A light beam with azimuthal polarization and flipped sign of OAM will be generated when changing the polarization state of incident light from RCP to LCP.

The metasurfaces have the metal-dielectric-metal configuration with the top layer of nanorods with space-variant orientation (Fig. 2a). The gold ground layer and SiO₂ spacer layer are deposited on a silicon substrate by electron beam evaporation. The top layer of nanorods is

fabricated using electron-beam lithography and standard lift-off process, and a 3-nm-Ti layer is deposited between the top layer and the SiO₂ spacer layer for adhesion purpose. In previous works, the residual part is minimized and the converted part is maximized when the metasurface functions as a perfect half-wave plate by optimizing the design parameters. To obtain an operating wavelength where the converted and residual part have equal components, we modify the design parameters in Ref.19 specifically. For example, in order to target the operating wavelength of 700 nm, we fabricate a series of metasurfaces with all widths of nanorods uniformly biased from their ideal design values in steps of 10 nm. The orientation angles of nanorods are governed by the following expression

$$\alpha(r, \phi) = \phi + \alpha_0 + \frac{\pi}{4} \quad (1)$$

where (r, ϕ) is the polar coordinate representation. α_0 is the initial angle related to the phase difference of two eigenstates. The additional term $\frac{\pi}{4}$ in Eq. (1) is explained in the Supplementary section 2. To clearly illustrate the mechanism, the metasurface is illuminated at normal incidence by an LCP beam with a normalized Jones vector $\frac{1}{\sqrt{2}} \begin{bmatrix} 1 \\ -i \end{bmatrix}$. At a particular location of azimuthal angle ϕ , the polarization state of the resultant beam is generally a superposition of two components with orthogonal circular polarization states, i.e., the converted part with an abrupt phase change E_{Con}^{LCP} and the residual part without phase delay E_{Res}^{LCP} . The expression for the superposition is given by

$$E_{out}^{LCP} = (E_{Con}^{LCP} + E_{Res}^{LCP}) = \frac{1}{\sqrt{2}} \left(\frac{A}{A+B} e^{i(\frac{\pi}{2}-2\phi)} \begin{bmatrix} 1 \\ -i \end{bmatrix} + \frac{B}{A+B} \begin{bmatrix} 1 \\ i \end{bmatrix} \right) \quad (2)$$

Apart from the Ohm loss and absorption, all of the reflected beams contribute to VVB generation. A and B represent the amplitudes of converted and residual light, respectively. If we tune the reflection properties of the gold nanorods to have $A = B$, the resultant beam gives rise to the linearly polarized light and also acquires a phase change. Its Jones vector is given by

$$E_{out}^{LCP} = \sqrt{2}e^{i(\frac{\pi}{4}-\phi)} \begin{bmatrix} \cos(\frac{\pi}{4}-\phi) \\ \sin(\frac{\pi}{4}-\phi) \end{bmatrix} \quad (3)$$

A similar derivation takes place when the polarization state of the incident light is RCP. The Jones vector of emerging beam is

$$E_{out}^{RCP} = \sqrt{2}e^{i(\frac{\pi}{4}+\phi)} \begin{bmatrix} \cos(\frac{\pi}{4}+\phi) \\ -\sin(\frac{\pi}{4}+\phi) \end{bmatrix} \quad (4)$$

The superscripts in Eqs. (2-4) represent the polarization states of the incident light. Figure 2b shows the polarization and the phase evolution when a circularly polarized incident light is incident upon a metasurface. If $A \neq B$, the resultant beam is elliptically polarized with an additional phase change. More details about polarization and phase evolution can be found in the Supplementary section 1. In brief, our metasurface is able to generate a structured beam from an unstructured one by using the spin-orbit coupling. What's more, there is a global phase factor, in the above case $\exp(i(\phi + \pi/4))$, appears together with the polarization distribution. Therefore, the resultant beam carries orbital angular momentum $\ell = 1$ as well. The nanorod distribution and polarization distribution of the emerging beam for different α_0 can be found in Fig. S2 (supplementary section 2).

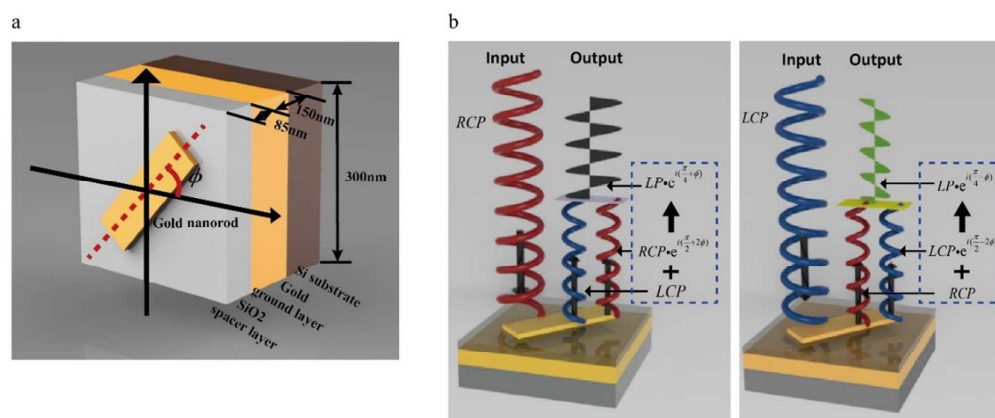


Figure 2. Illustration of the single-pixel cell structure and the polarization conversion of the emerging light. (a) The reflective-type half-wave plate consists of three layers: the ground gold layer (150 nm),

1
2
3 the SiO₂ spacer layer (85 nm) and the top layer of gold nanorods (30 nm). Each pixel size is 300 nm by
4 300 nm. Each nanorod is 200 nm in length, 90 nm in width and 30 nm in thickness. (b) For the
5 circularly polarized incident light, the emerging light is the superposition of two orthogonal circularly
6 polarized beams corresponding to the converted part (same helicity with the incident beam) and
7 residual part (opposite helicity with the incident beam), respectively. When the converted part and the
8 residual part have equal components, the output beam gives rise to the linearly polarized light. Spiral
9 curves in red colour stands for the right-handed circularly polarized light (RCP), and that in blue colour
10 stands for the left-handed circularly polarized light (LCP).
11
12
13
14
15
16
17
18

19 RESULTS

20
21 We design and fabricate two metasurfaces with different values of α_0 . For the reflective-type
22 metasurface configuration, the size of nanorod, the refractive index and thickness of spacer
23 layer, and the size of unit pixel affect the efficiency at a fixed wavelength significantly.
24 Furthermore, the fabrication error (e.g., nanorod distortion and missing nanorods) and the
25 film quality (e.g., cracks) would also lead to the disagreement between the numerical
26 simulation and experiment results. Fig. 3a shows the measured normalized power of the two
27 eigenstates over a wide range of wavelengths. The experimental value of Ohmic loss at the
28 resonance frequency of nanorod is less than 20% for the metal-dielectric-metal configuration.
29 Since our main concern is the about the operating wavelength where the converted and
30 non-converted parts have equal intensities, the two curves for the converted and residual parts
31 are normalized to the sum of these two components. The two curves overlap at the
32 wavelength of 697 nm, which means that the converted and residual part have equal
33 components at this wavelength and the VVB is realized. By passing through a linear polarizer
34 with different transmission angle, the generated structured beams from the fabricated
35 metasurfaces are characterized and validated. Figure 3b shows the simulated and measured
36 intensity distribution of vectorial vortex after passing through an analysing polarizer in
37 horizontal, 45°, vertical, and - 45° orientations at the wavelength of 697 nm. The appearance
38 of 's' shape patterns is theoretically predicted and experimentally confirmed. The observed
39 patterns indicate that the resultant beams indeed have an inhomogeneous polarization
40 distribution and a helical wavefront. The intensity patterns of vector beams with different
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

OAM can be found in supplementary Figure S3 (supplementary section 3). Moreover, the twisted direction of the 's' shape varying with the helicity of circular polarization are also experimentally confirmed from the obtained intensity patterns.


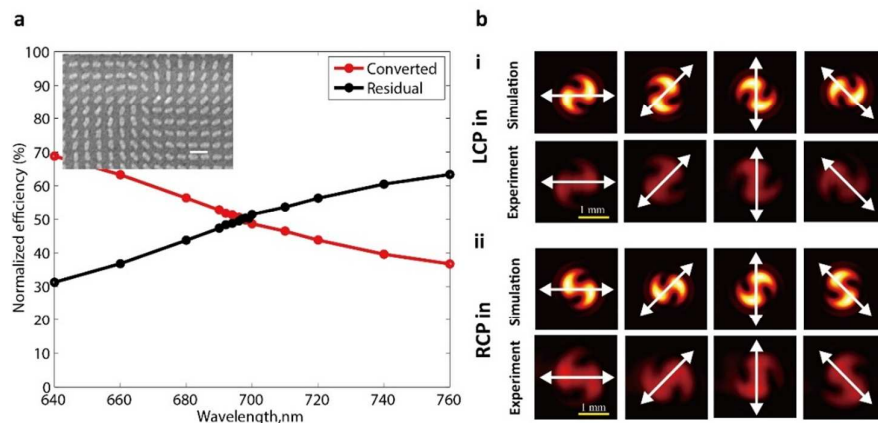


Figure 3. Measured power (normalized) of converted and residual parts at various wavelengths, and intensity patterns of vector vortex beam after passing through a linear polarizer. (a) The measured power (normalized) of converted and residual parts at various wavelengths. The inset is the scanning electron microscopy image of the metasurface for vector vortex beam generation. The scale bar is 500 nm. (b) Simulated and experimentally recorded intensity profile of the vector vortex beam after passing through a polarizer with different polarization angles including horizontal, diagonal, vertical and antidiagonal directions. The polarization angles are denoted by white double-headed arrows. i, LCP light input, ii, RCP light input.

The vector vortex beam can be considered as a superposition of two beams with different circular polarizations, which can be separated by using a phase gradient metasurface (PGM) since different circular polarizations are steered in two directions due to the generated Pancharatnam–Berry phase at the interface. Detailed explanation can be found in the Supplementary section 4. We employ a PGM, without the need of any additional polarizer and waveplate, to simultaneously decompose the output beam from the metasurface. The schematic of experimental setup is depicted in Fig. 4a. Here, the metasurface sample for the VVB generation is mounted on a three-dimensional translation stage and exposed to the light from tunable NKT supercontinuum laser. A Glan polarizer (GP) and a quarter-wave plate (QWP) are used to generate the required circularly polarized light. Then the light is

1
2
3
4 weakly focused by a lens with a focal length of 100 mm onto the metasurface to ensure that
5 the beam size is smaller than the sample. In order to collect the reflected light, a
6 polarization-insensitive beam-splitter (BS) is inserted between the QWP and the lens. The
7 reflected vector vortex beam is either projected to PGM to decompose the resultant beam, or
8 propagates in the free space for further application. The SEM images of PGM is shown in Fig.
9 4a (see inset). The simulated and obtained intensity distributions of two components are
10 shown in Fig. 4b. The doughnut shape and singular point confirm the existence of optical
11 vortex (right in Fig. 4b), which corresponds to the converted light. The residual part (left in
12 Fig. 4b), on the other hand, is confirmed by the shape without a singularity in the light spot.
13 To further reveal the spiral wavefront and verify the OAM of optical vortex, the PGM is
14 replaced by the circular polarization filter consisting of a quarter-wave plate and a linear
15 polarizer. We deliberately let both of the converted and residual beam partially pass the filter
16 by tuning the angle of quarter-wave plate and linear polarizer. The residual beam serves as the
17 reference spherical wave to interfere with the converted vortex beam. The double helical
18 intensity profile and the number of branches stemming from the singularity confirm that the
19 converted beam carries orbital angular momentum of $2\hbar$ (Fig.4 c).

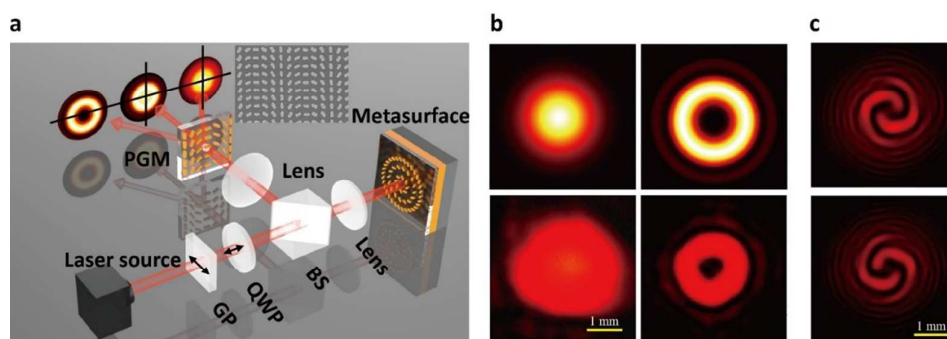

20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Figure 4. Experimental setup, and the theoretically predicted and measured intensity distribution of the two components. (a) Schematic of the experimental setup. The desired circularly polarized light is generated by passing a laser beam (NKT-SuperK EXTREME) through properly oriented glan polarizer (GP) and quarter-wave plate (QWP), then normally illuminated upon metasurface with weak focus. In order to collect the reflected light and project it to a phase-gradient metasurface (PGM), a polarization insensitive beam splitter (BS) is inserted between QWP and lens. A charge coupled device (CCD)

1
2
3 camera is used to image the output beams. The inset is the SEM image of fabricated phase-gradient
4 metasurface. (b) Simulated (top) and measured (bottom) intensity profiles of the two components. (c)
5
6
7 Spiral patterns created by the interference of the vortex beam and a co-propagating Gaussian beam.
8
9 The polarization states of incident light are LCP (upper image) and RCP (lower image), respectively.
10

11 **DISCUSSION**

12
13
14 Efficient generation of the structured optical fields using an ultra-compact device has both
15
16 fundamental and technical importance for photonics related research. As promising
17
18 candidates for integrated optics, metasurfaces have opened a broad range of applications for
19
20 inhomogeneous control amplitude, phase, and polarization of the scattered waves. The
21
22 proposed method provides an unusual way to generate vector vortex beam carrying orbital
23
24 angular momentum using a single metasurface, which will inspire the pursuit of further novel
25
26 functionalities. To our knowledge, this is the first time that the converted part and the residual
27
28 part are used together to realize new functionalities to achieve the most efficient light
29
30 utilization. Both the phase and polarization are manipulated at subwavelength scale by the
31
32 artificial array of engineered nanorods over the metasurface. On the other hand, both the
33
34 polarization distribution and the orbital angular momentum of the output wave are controlled
35
36 by the helicity of the incident light polarization. We develop two metasurfaces with different
37
38 initial angles ($\alpha_0 = 0$ and $\alpha_0 = \pi$), which can generate radially and azimuthally polarized
39
40 vortices carrying orbital angular momenta, respectively. The SEM image of the other
41
42 metasurface with $\alpha_0 = \pi$ and results are available in Fig. S5 (supplementary section 5). The
43
44 good agreement between predicted and experimental results confirms the proposed
45
46 methodology. It has been reported that azimuthally polarized beams with helical wavefront
47
48 could effectively achieve a significantly smaller spot than normal azimuthally polarized
49
50 beams when focused with a high-numerical-aperture objective.

51
52 For the application of free space communication, the optical vortex has attracted growing
53
54 attention due to its higher data transmission capacity. However, the atmospheric turbulence
55
56 strongly affects the properties of the optical vortex when propagating in free space. The
57
58 existence of the vectorial vortex can be identified with longer propagation distance through
59
60

1
2
3 atmosphere than the scalar vortex even with vanishing characteristic vortex structure. By
4 carefully designing the angle distribution of nanorods, any polarization state can be realized
5 using a single metasurface with the circularly polarized incident light. In addition, the angle
6 of resultant polarization is switchable by controlling the helicity of the circularly polarized
7 incident light.
8
9

10
11
12 In summary, we propose and experimentally demonstrate an approach to generate vector
13 vortex beams using a single plasmonic metasurface. The uniqueness of the proposed
14 method lies in the combined action of the Pancharatnam-Berry phase and the superposition of
15 two orthogonal circularly polarized light beams. Both orbital angular momentum and
16 polarization distribution in transverse plane about propagation axis are manipulated by a
17 single metasurface consisting of nanorods with spatially variant orientation. As our work
18 solves several major issues typically associated with VVB generation: poor resolution, low
19 damage threshold, bulky size and complicated experimental setup, it opens a new window for
20 future practical applications of the structured beams in the relevant research fields such
21 as optical communication, particle trapping, microscopy and quantum optics.
22
23
24
25
26
27
28
29
30
31
32

33 34 35 **ACKNOWLEDGMENTS**

36 This work is supported by the Engineering and Physical Sciences Research Council of the
37 United Kingdom (Grant Ref: EP/M003175/1).
38
39
40

41 42 **AUTHOR INFORMATION**

43 44 **Corresponding Author**

45 * Email: x.chen@hw.ac.uk

46 Note: F. Yue and D. Wen contribute equally to this work.
47
48

49 50 **SUPPORTING INFORMATION**

51 The Supporting Information is available free of charge on the ACS Publications website at
52 DOI: 10.1021/acsphotonics.XXXXXXX.
53
54
55
56
57
58
59
60

REFERENCES

- (1) Parigi, V.; D'Ambrosio, V.; Arnold, C.; Marrucci, L.; Sciarrino, F.; Laurat, J., Storage and retrieval of vector beams of light in a multiple-degree-of-freedom quantum memory. *Nat. Commun.* **2015**, *6*, 7706.
- (2) Ng, J.; Lin, Z. F.; Chan, C. T., Theory of Optical Trapping by an Optical Vortex Beam. *Phys. Rev. Lett.* **2010**, *104*, 103601.
- (3) D'Ambrosio, V.; Nagali, E.; Walborn, S. P.; Aolita, L.; Slussarenko, S.; Marrucci, L.; Sciarrino, F., Complete experimental toolbox for alignment-free quantum communication. *Nat. Commun.* **2012**, *3*.
- (4) Vallone, G.; D'Ambrosio, V.; Sponselli, A.; Slussarenko, S.; Marrucci, L.; Sciarrino, F.; Villoresi, P., Free-Space Quantum Key Distribution by Rotation-Invariant Twisted Photons. *Phys. Rev. Lett.* **2014**, *113*.
- (5) Hao, X. A.; Kuang, C. F.; Wang, T. T.; Liu, X., Phase encoding for sharper focus of the azimuthally polarized beam. *Opt. Lett.* **2010**, *35*, 3928-3930.
- (6) Dorn, R.; Quabis, S.; Leuchs, G., Sharper Focus for a Radially Polarized Light Beam. *Phys. Rev. Lett.* **2003**, *91*, 233901.
- (7) Kang, M.; Chen, J.; Wang, X. L.; Wang, H. T., Twisted vector field from an inhomogeneous and anisotropic metamaterial. *J. Opt. Soc. Am. B* **2012**, *29*, 572-576.
- (8) Bauer, T.; Orlov, S.; Peschel, U.; Banzer, P.; Leuchs, G., Nanointerferometric amplitude and phase reconstruction of tightly focused vector beams. *Nat. Photonics* **2013**, *8*, 23-27.
- (9) Cardano, F.; Karimi, E.; Slussarenko, S.; Marrucci, L.; de Lisio, C.; Santamato, E., Polarization pattern of vector vortex beams generated by q-plates with different topological charges. *Appl. Opt.* **2012**, *51*, C1-C6.
- (10) Rumala, Y. S.; Milione, G.; Nguyen, T. A.; Pratavieira, S.; Hossain, Z.; Nolan, D.; Slussarenko, S.; Karimi, E.; Marrucci, L.; Alfano, R. R., Tunable supercontinuum light vector vortex beam generator using a q-plate. *Opt. Lett.* **2013**, *38*, 5083-5086.

- 1
2
3 (11) Beresna, M.; Gecevicius, M.; Kazansky, P. G.; Gertus, T., Radially polarized optical
4 vortex converter created by femtosecond laser nanostructuring of glass. *Appl. Phys. Lett.*
5 **2011**, *98*, 201101.
6
7
8
9 (12) Yin, X.; Ye, Z.; Rho, J.; Wang, Y.; Zhang, X., Photonic spin Hall effect at metasurfaces.
10 *Science* **2013**, *339*, 1405-1407.
11
12
13 (13) Ni, X.; Wong, Z. J.; Mrejen, M.; Wang, Y.; Zhang, X., An ultrathin invisibility skin
14 cloak for visible light. *Science* **2015**, *349*, 1310-1314.
15
16
17 (14) Yu, N.; Capasso, F., Flat optics with designer metasurfaces. *Nat. Mater.* **2014**, *13*,
18 139-150.
19
20
21 (15) Lin, D.; Fan, P.; Hasman, E.; Brongersma, M. L., Dielectric gradient metasurface
22 optical elements. *Science* **2014**, *345*, 298-302.
23
24
25 (16) Chen, X.; Huang, L.; Muhlenbernd, H.; Li, G.; Bai, B.; Tan, Q.; Jin, G.; Qiu, C. W.;
26 Zhang, S.; Zentgraf, T., Dual-polarity plasmonic metalens for visible light. *Nat. Commun.*
27 **2012**, *3*, 1198.
28
29
30 (17) Aieta, F.; Kats, M. A.; Genevet, P.; Capasso, F., Multiwavelength achromatic
31 metasurfaces by dispersive phase compensation. *Science* **2015**, *347*, 1342-1345.
32
33
34 (18) Zhu, W.; Song, Q.; Yan, L.; Zhang, W.; Wu, P. C.; Chin, L. K.; Cai, H.; Tsai, D. P.; Shen,
35 Z. X.; Deng, T. W., A flat lens with tunable phase gradient by using random access
36 reconfigurable metamaterial. *Adv. Mater.* **2015**, *27*, 4739-4743.
37
38
39 (19) Zheng, G. X.; Muhlenbernd, H.; Kenney, M.; Li, G. X.; Zentgraf, T.; Zhang, S.,
40 Metasurface holograms reaching 80% efficiency. *Nat. Nanotechnol.* **2015**, *10*, 308-312.
41
42
43 (20) Wen, D.; Yue, F.; Li, G.; Zheng, G.; Chan, K.; Chen, S.; Chen, M.; Li, K. F.; Wong, P. W.;
44 Cheah, K. W.; Yue Bun Pun, E.; Zhang, S.; Chen, X., Helicity multiplexed broadband
45 metasurface holograms. *Nat. Commun.* **2015**, *6*, 8241.
46
47
48 (21) Yirmiyahu, Y.; Niv, A.; Biener, G.; Kleiner, V.; Hasman, E., Vectorial vortex mode
49 transformation for a hollow waveguide using Pancharatnam-Berry phase optical elements.
50 *Opt. Lett.* **2006**, *31*, 3252-3254.
51
52
53 (22) Marrucci, L.; Manzo, C.; Paparo, D., Pancharatnam-Berry phase optical elements
54 for wave front shaping in the visible domain: Switchable helical mode generation. *Appl.*
55 *Phys. Lett.* **2006**, *88*, 221102.
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- (23) Cardano, F.; Marrucci, L., Spin-orbit photonics. *Nat. Photonics* **2015**, *9*, 776-778.
- (24) Bliokh, K. Y.; Rodriguez-Fortuno, F. J.; Nori, F.; Zayats, A. V., Spin-orbit interactions of light. *Nat. Photonics* **2015**, *9*, 796-808.
- (25) Karimi, E.; Schulz, S. A.; De Leon, I.; Qassim, H.; Upham, J.; Boyd, R. W., Generating optical orbital angular momentum at visible wavelengths using a plasmonic metasurface. *Light Sci. Appl.* **2014**, *3*, e167.
- (26) Huang, L.; Chen, X.; Muhlenbernd, H.; Li, G.; Bai, B.; Tan, Q.; Jin, G.; Zentgraf, T.; Zhang, S., Dispersionless phase discontinuities for controlling light propagation. *Nano Lett.* **2012**, *12*, 5750-5755.
- (27) Yang, Y. M.; Wang, W. Y.; Moitra, P.; Kravchenko, I. I.; Briggs, D. P.; Valentine, J., Dielectric Meta-Reflectarray for Broadband Linear Polarization Conversion and Optical Vortex Generation. *Nano Lett.* **2014**, *14*, 1394-1399.
- (28) Mehmood, M.; Mei, S.; Hussain, S.; Huang, K.; Siew, S.; Zhang, L.; Zhang, T.; Ling, X.; Liu, H.; Teng, J., Visible Frequency Metasurface for Structuring and Spatially Multiplexing Optical Vortices. *Adv. Mater.* **2016**.
- (29) Pu, M.; Li, X.; Ma, X.; Wang, Y.; Zhao, Z.; Wang, C.; Hu, C.; Gao, P.; Huang, C.; Ren, H., Catenary optics for achromatic generation of perfect optical angular momentum. *Sci. Adv* **2015**, *1*, e1500396.
- (30) Li, X.; Pu, M.; Zhao, Z.; Ma, X.; Jin, J.; Wang, Y.; Gao, P.; Luo, X., Catenary nanostructures as compact Bessel beam generators. *Sci. Rep.* **2016**, *6*.
- (31) Qin, F.; Ding, L.; Zhang, L.; Monticone, F.; Chum, C. C.; Deng, J.; Mei, S.; Li, Y.; Teng, J.; Hong, M., Hybrid bilayer plasmonic metasurface efficiently manipulates visible light. *Sci. Adv* **2016**, *2*, e1501168.
- (32) Monticone, F.; Estakhri, N. M.; Alù, A., Full control of nanoscale optical transmission with a composite metascreen. *Phys. Rev. Lett.* **2013**, *110*, 203903.
- (33) Yi, X. N.; Ling, X. H.; Zhang, Z. Y.; Li, Y.; Zhou, X. X.; Liu, Y. C.; Chen, S. Z.; Luo, H. L.; Wen, S. C., Generation of cylindrical vector vortex beams by two cascaded metasurfaces. *Opt. Express* **2014**, *22*, 17207-17215.

1
2
3 (34) Huang, L.; Chen, X.; Mühlenbernd, H.; Li, G.; Bai, B.; Tan, Q.; Jin, G.; Zentgraf, T.;
4 Zhang, S., Dispersionless phase discontinuities for controlling light propagation. *Nano Lett.*
5 **2012**, *12*, 5750-5755.
6
7
8
9

10
11
12 **For Table of Contents Use Only**
13

14
15
16 **Vector Vortex Beam Generation with a Single Plasmonic**
17
18 **Metasurface**
19


20
21 **Fuyong Yue¹, Dandan Wen¹, Jingtao Xin², Brian D. Gerardot¹, Jensen Li³, Xianzhong Chen^{1*}**
22

23 *1. SUPA, Institute of Photonics and Quantum Sciences, School of Engineering and Physical*
24 *Sciences,*

25 *Heriot-Watt University, Edinburgh, EH14 4AS, UK*

26
27 *2. Beijing Engineering Research Centre of Optoelectronic Information and Instruments, Beijing*
28 *Information Science and Technology University, Beijing, 100192, China*

29 *3. School of Physics and Astronomy, University of Birmingham, B15 2TT*
30
31

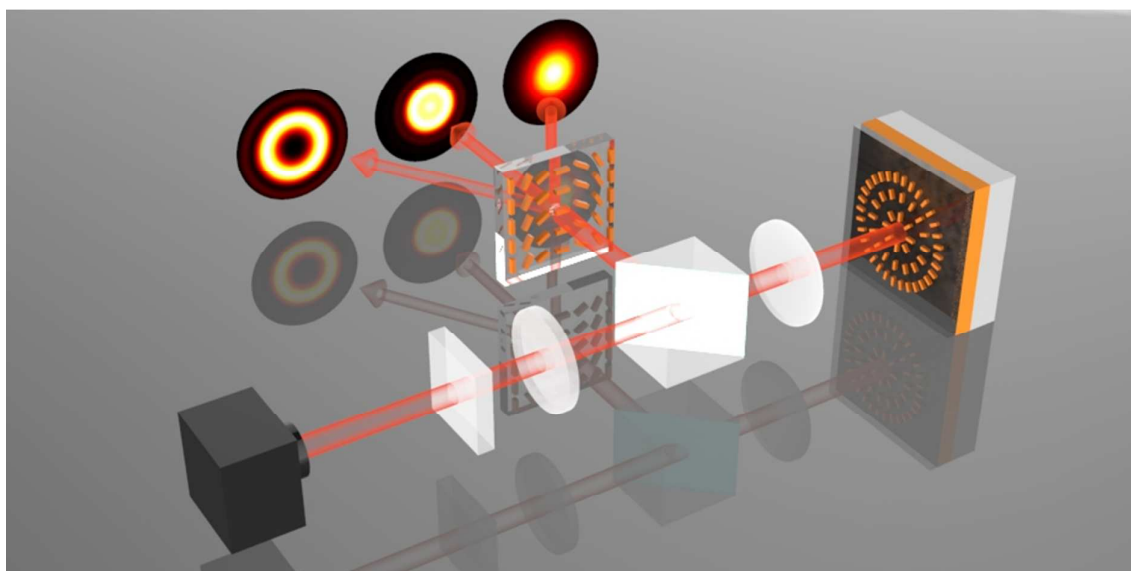

52 **Description:**

53
54 The generation of vector vortex beams (VVBs) using metasurface is based on the superposition
55 of the converted part with an additional phase pickup and the residual part without a phase
56 change. By maintaining the equal components for the converted part and the residual part, the
57
58
59
60

1
2
3 cylindrically polarized vortex beams carrying orbital angular momentum are experimentally
4 demonstrated based on a single metasurface at subwavelength scale. The vector vortex beam
5 can be considered as a superposition of two opposite circularly polarized beams carrying
6 different OAM. A phase gradient metasurface is used to separate the generated VVBs to two
7 beams with different circular polarizations.
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60