



Heriot-Watt University  
Research Gateway

## Halogen effects on the solid-state packing of phenylalanine derivatives and the resultant gelation properties

### Citation for published version:

Ramalhete, SM, Foster, J, Green, H, Nartowski, KP, Heinrich, M, Martin, PC, Khimyak, YZ & Lloyd, GO 2017, 'Halogen effects on the solid-state packing of phenylalanine derivatives and the resultant gelation properties', *Faraday Discussions*. <https://doi.org/10.1039/C7FD00108H>

### Digital Object Identifier (DOI):

[10.1039/C7FD00108H](https://doi.org/10.1039/C7FD00108H)

### Link:

[Link to publication record in Heriot-Watt Research Portal](#)

### Document Version:

Peer reviewed version

### Published In:

Faraday Discussions

### General rights

Copyright for the publications made accessible via Heriot-Watt Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

### Take down policy

Heriot-Watt University has made every reasonable effort to ensure that the content in Heriot-Watt Research Portal complies with UK legislation. If you believe that the public display of this file breaches copyright please contact [open.access@hw.ac.uk](mailto:open.access@hw.ac.uk) providing details, and we will remove access to the work immediately and investigate your claim.

## Halogen effects on the solid-state packing of phenylalanine derivatives and the resultant gelation properties

Susana M. Ramalhete,<sup>a</sup> Jamie S. Foster,<sup>b</sup> Hayley R. Green,<sup>b</sup> Karol P. Nartowski,<sup>a</sup> Margaux Heinrich,<sup>b</sup> Peter C. Martin,<sup>c</sup> Yaroslav Z. Khimyak\*<sup>a</sup> and Gareth O. Lloyd\*<sup>b</sup>

<sup>a.</sup> *Department of Pharmaceutical Science School of Pharmacy, University of East Anglia, Norwich, United Kingdom, NR4 7TJ, E-mail: Y.Khimyak@uea.ac.uk.*

<sup>b.</sup> *Institute of Chemical Sciences, School of Engineering and Physical Sciences, Heriot-Watt University, Edinburgh, Scotland, United Kingdom, EH14 4AS, E-mail: G.O.Lloyd@hw.ac.uk*

<sup>c.</sup> *Department of Chemistry, Cambridge University, Lensfield Road, Cambridge, United Kingdom, CB2 1EW.*

CCDC 1532628-1532632

-----  
Summary of Data CCDC 1532628  
-----

Compound Name:

Formula: C<sub>9</sub> H<sub>9</sub> F<sub>2</sub> N<sub>1</sub> O<sub>2</sub>,H<sub>2</sub> O<sub>1</sub>

Unit Cell Parameters: a 13.100(3) b 5.4019(12) c 14.423(4) P21  
-----

-----  
Summary of Data CCDC 1532629  
-----

Compound Name:

Formula: C<sub>9</sub> H<sub>10</sub> Br<sub>1</sub> N<sub>1</sub> O<sub>2</sub>,H<sub>2</sub> O<sub>1</sub>

Unit Cell Parameters: a 6.3036(4) b 5.3042(3) c 15.9161(9) P21  
-----

-----  
Summary of Data CCDC 1532630  
-----

Compound Name:

Formula: C<sub>9</sub> H<sub>10</sub> F<sub>1</sub> N<sub>1</sub> O<sub>2</sub>,H<sub>2</sub> O<sub>1</sub>

Unit Cell Parameters: a 13.3028(14) b 5.4628(6) c 14.0151(15) P21  
-----

-----  
Summary of Data CCDC 1532631  
-----

Compound Name:

Formula: C<sub>9</sub> H<sub>10</sub> I<sub>1</sub> N<sub>1</sub> O<sub>2</sub>,H<sub>2</sub> O<sub>1</sub>

Unit Cell Parameters: a 5.3139(3) b 6.3152(4) c 32.741(2) P212121  
-----

-----  
Summary of Data CCDC 1532632  
-----

Compound Name:

Formula: C<sub>9</sub> H<sub>10</sub> Cl<sub>1</sub> N<sub>1</sub> O<sub>2</sub>,H<sub>2</sub> O<sub>1</sub>

Unit Cell Parameters: a 13.5539(8) b 5.4096(3) c 15.0157(9) P21

## NMR

					$T_1$ (s)		$C_{\alpha H}$	$C_{\beta H_2}$
					Arom			
		Phe	Cl-Phe H <sub>3,5</sub>	Cl-Phe H <sub>2,6</sub>	F-Phe H <sub>3,5</sub>	F-Phe H <sub>2,6</sub>		
Hydrogel	Phe	2.45 (0.14)	-	-	-	-	2.42 (0.15)	2.41 (0.15)
	Cl-Phe	-	2.75 (0.07)	2.17 (0.06)	-	-	2.10 (0.08)	0.93 (0.04)
	F-Phe	-	-	-	2.52 (0.07)	3.66 (0.02)	2.84 (0.15)	0.87 (0.01)
Solution	Phe	2.07 (0.02)	-	-	-	-	2.20 (0.03)	0.63 (0.01)
	Cl-Phe	-	3.74 (0.06)	2.34 (0.09)	-	-	2.65 (0.05)	0.70 (0.06)
	F-Phe	-	-	-	2.75 (0.03)	3.73 (0.02)	2.90 (0.04)	0.85 (0.02)

## Rheology

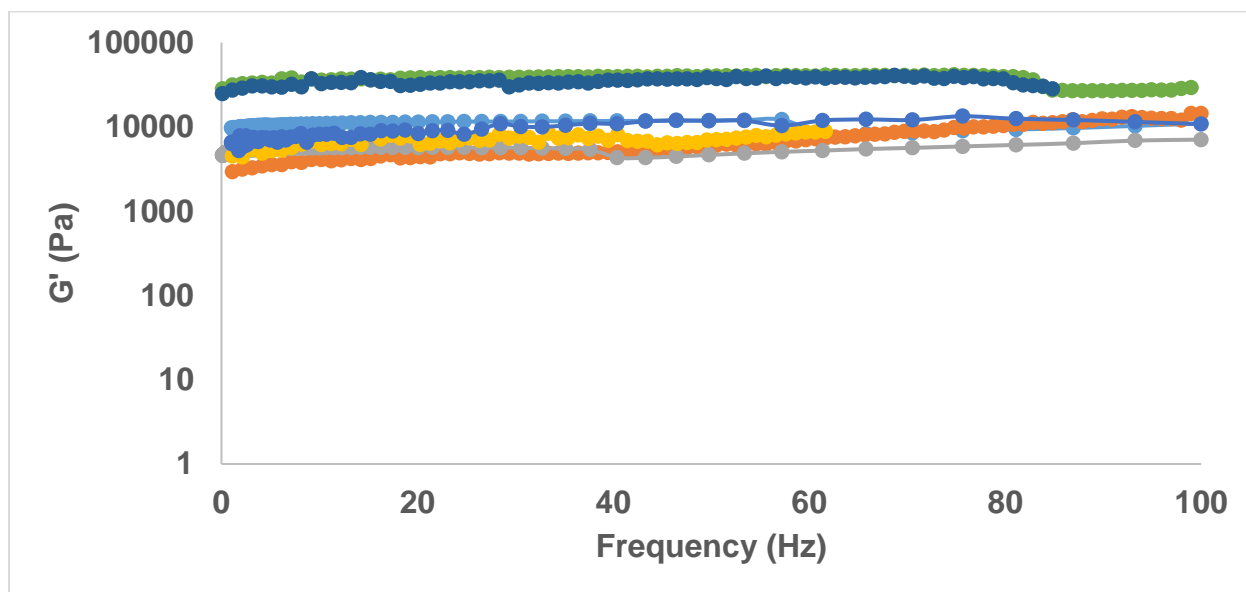


Fig. S1. Frequency sweeps of all gels in DMSO. Green, Br-Phe; Dark Blue, Phe, light blue, F-Phe; medium blue, 2Cl-Phe; light orange, Cl-Phe; grey, 5F-Phe; dark orange, 2F-Phe.

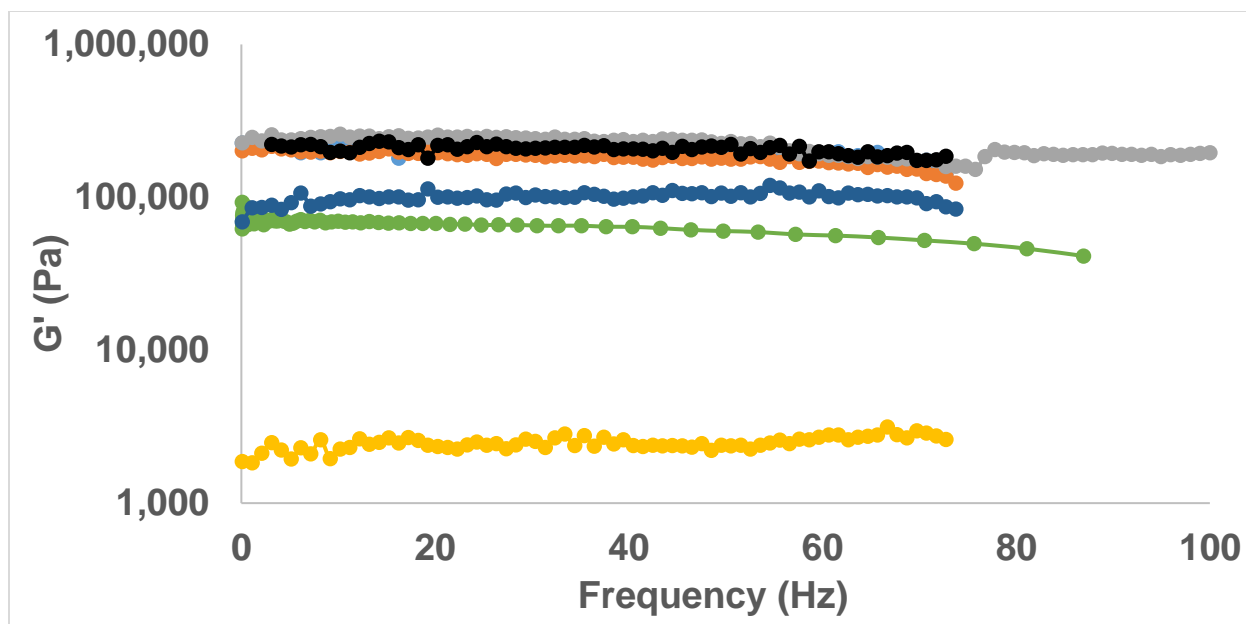


Fig. S2. Frequency sweeps of all gels in water. Green, Br-Phe; Dark Blue, Phe, light blue, F-Phe (only a few of the plotted data points are visible); medium blue, 2Cl-Phe; black, Cl-Phe; grey, 5F-Phe; dark orange, 2F-Phe.

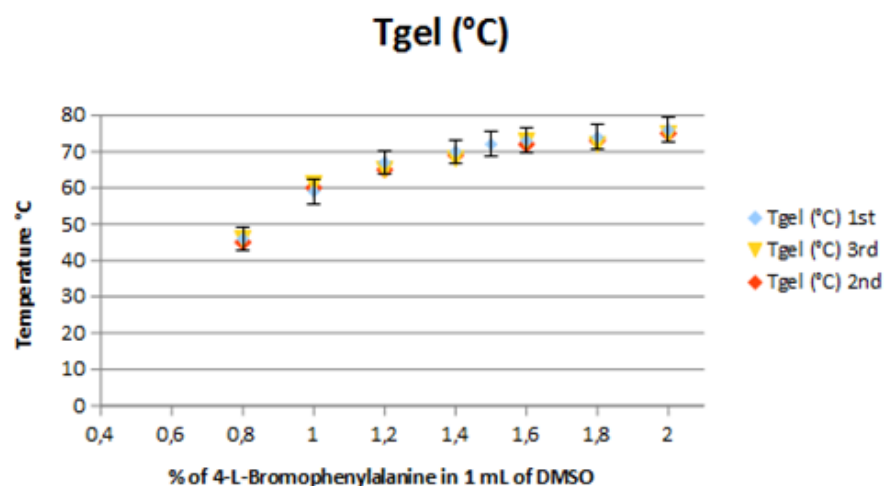


Fig. S3.  $T_{gel}$  determination of Br-Phe in DMSO.

## PXRD patterns

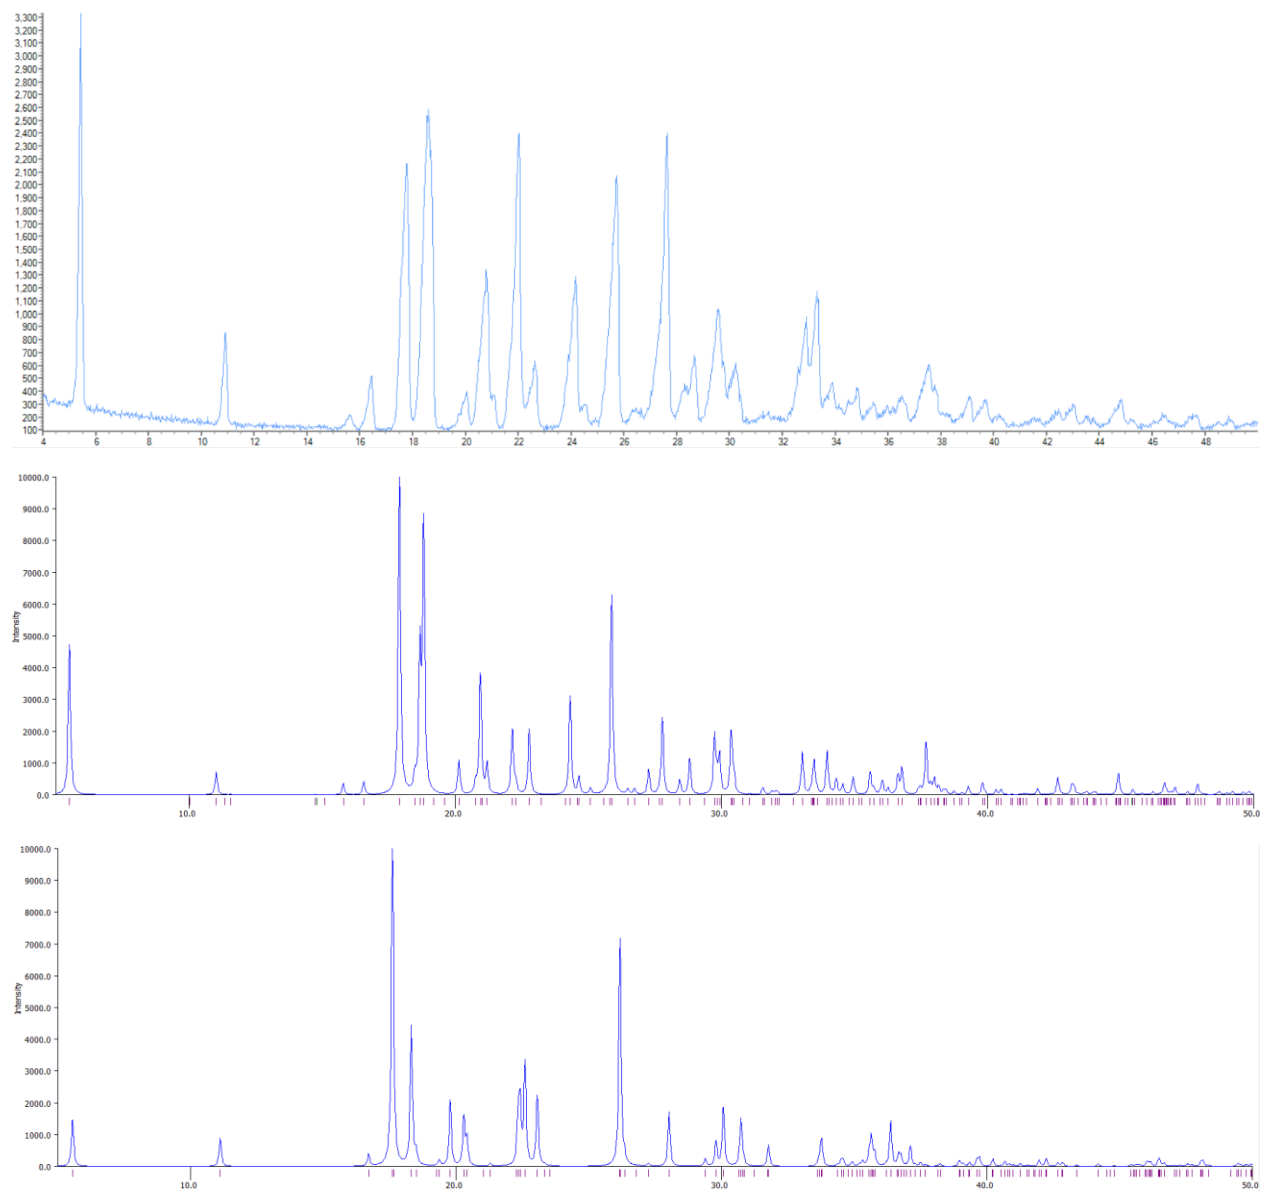


Fig. S4. F-Phe commercial sample matches the known form (EXAXEG) 2<sup>nd</sup> pattern, and not the other published form (DOMVUW).<sup>1</sup>

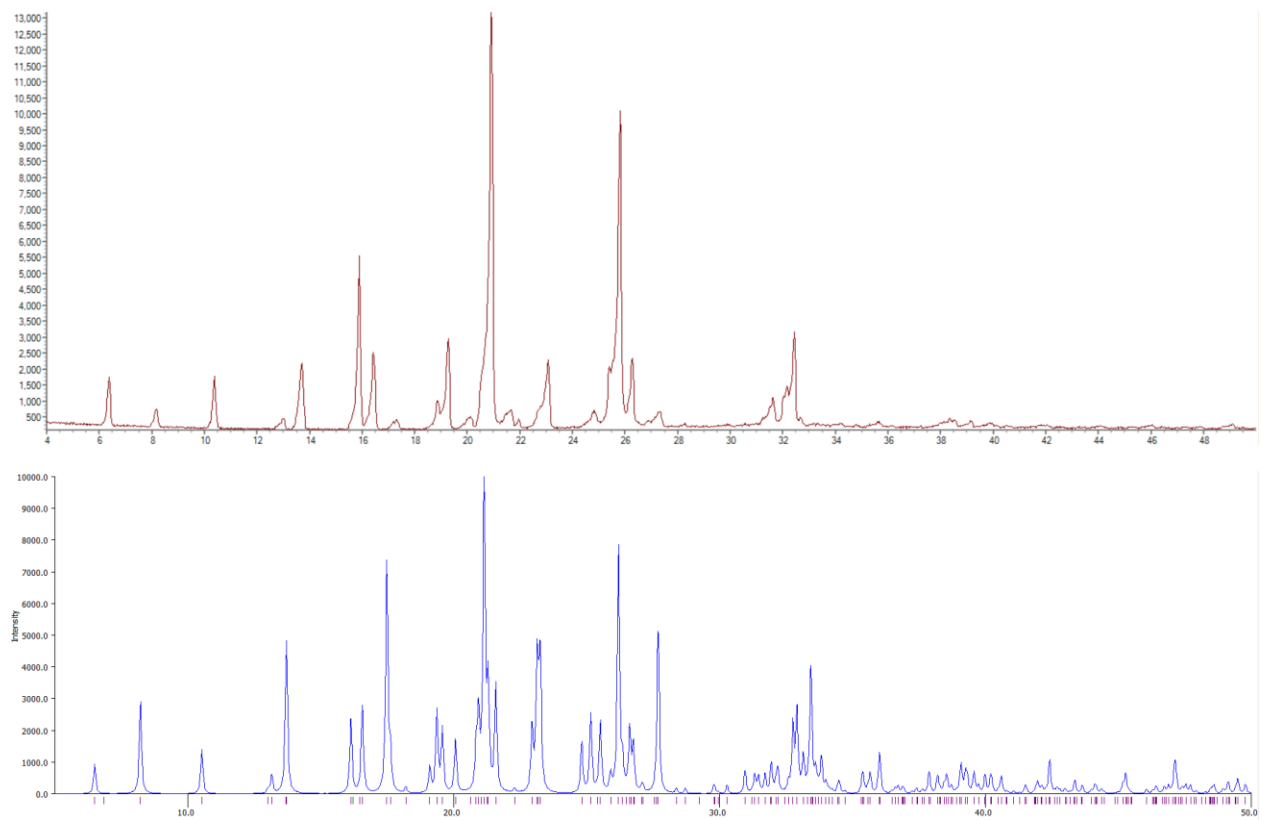


Fig. S5. F-Phe h<sub>2</sub>O gel pxrd sample top with single crystal data simulated pattern bottom.

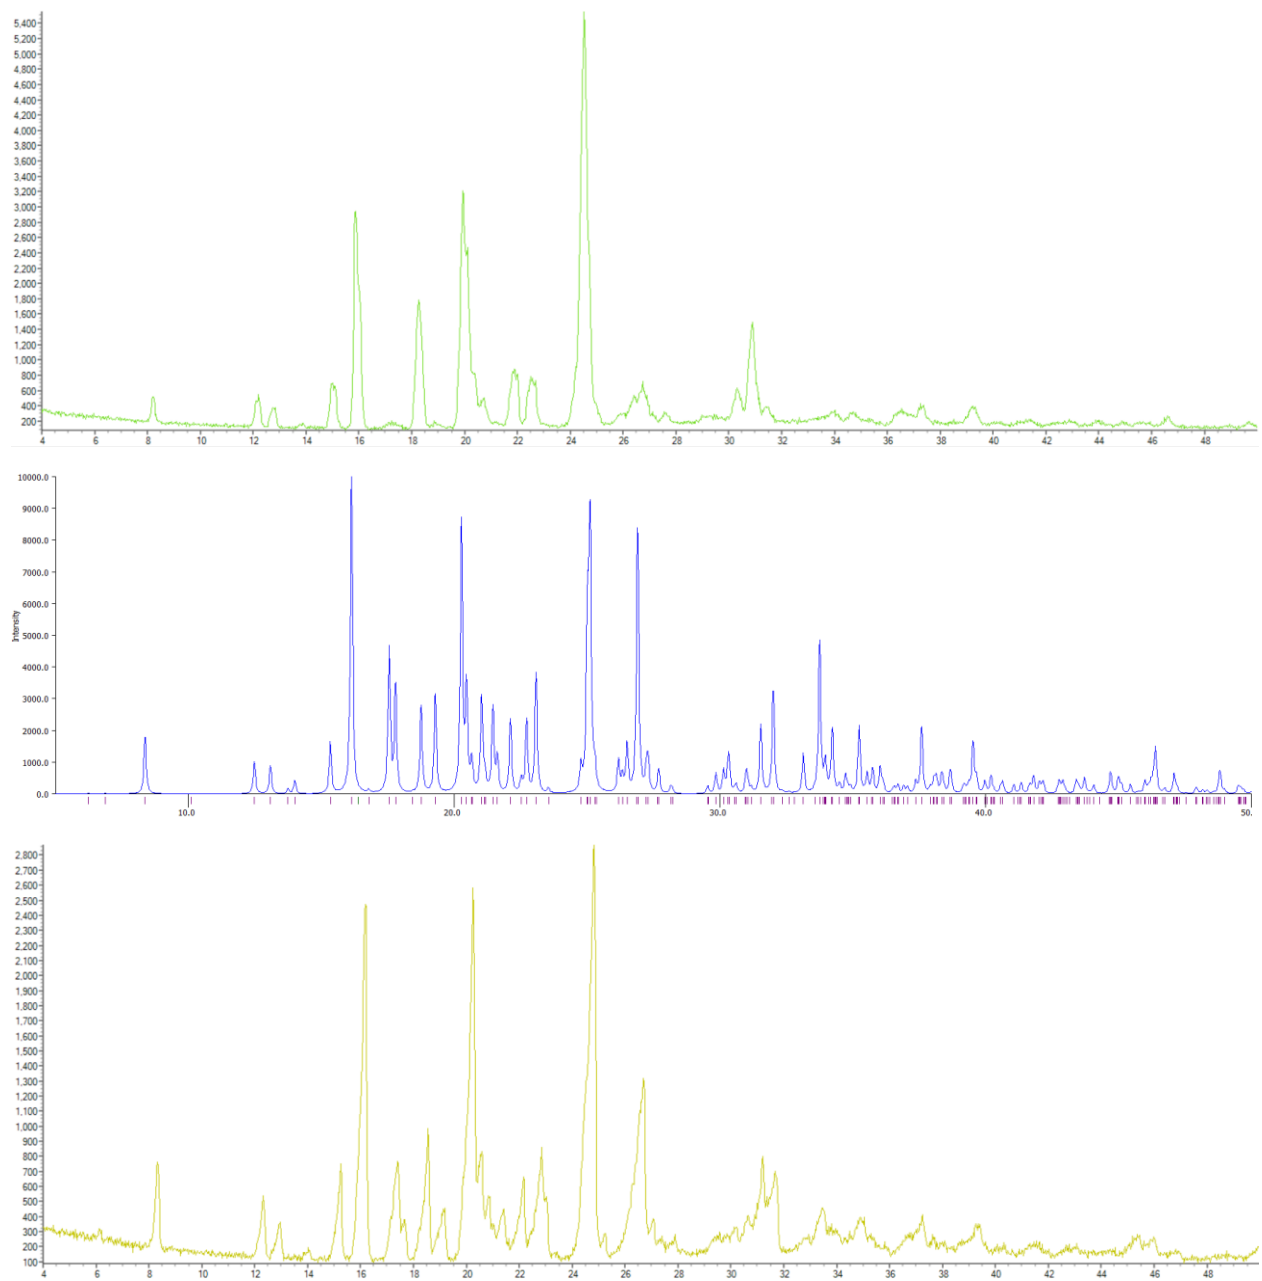


Fig. S6. 2F-Phe hydrogel PXRD sample top, simulated pattern from the single crystal data middle and commercial sample bottom (which appears to be the hydrate).

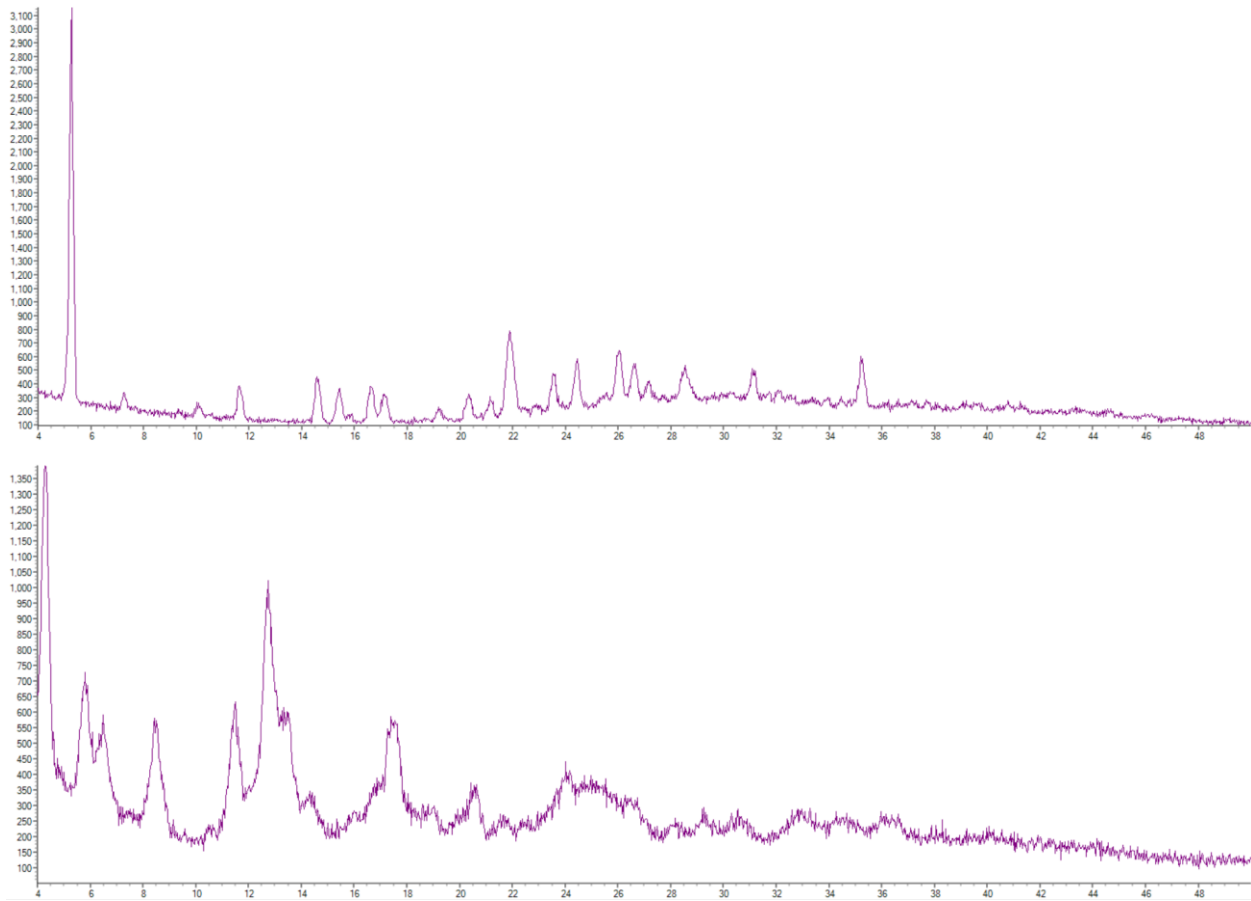


Fig. S7. 5F-Phe hydrogel PXRD sample above with commercial anhydrous form below.



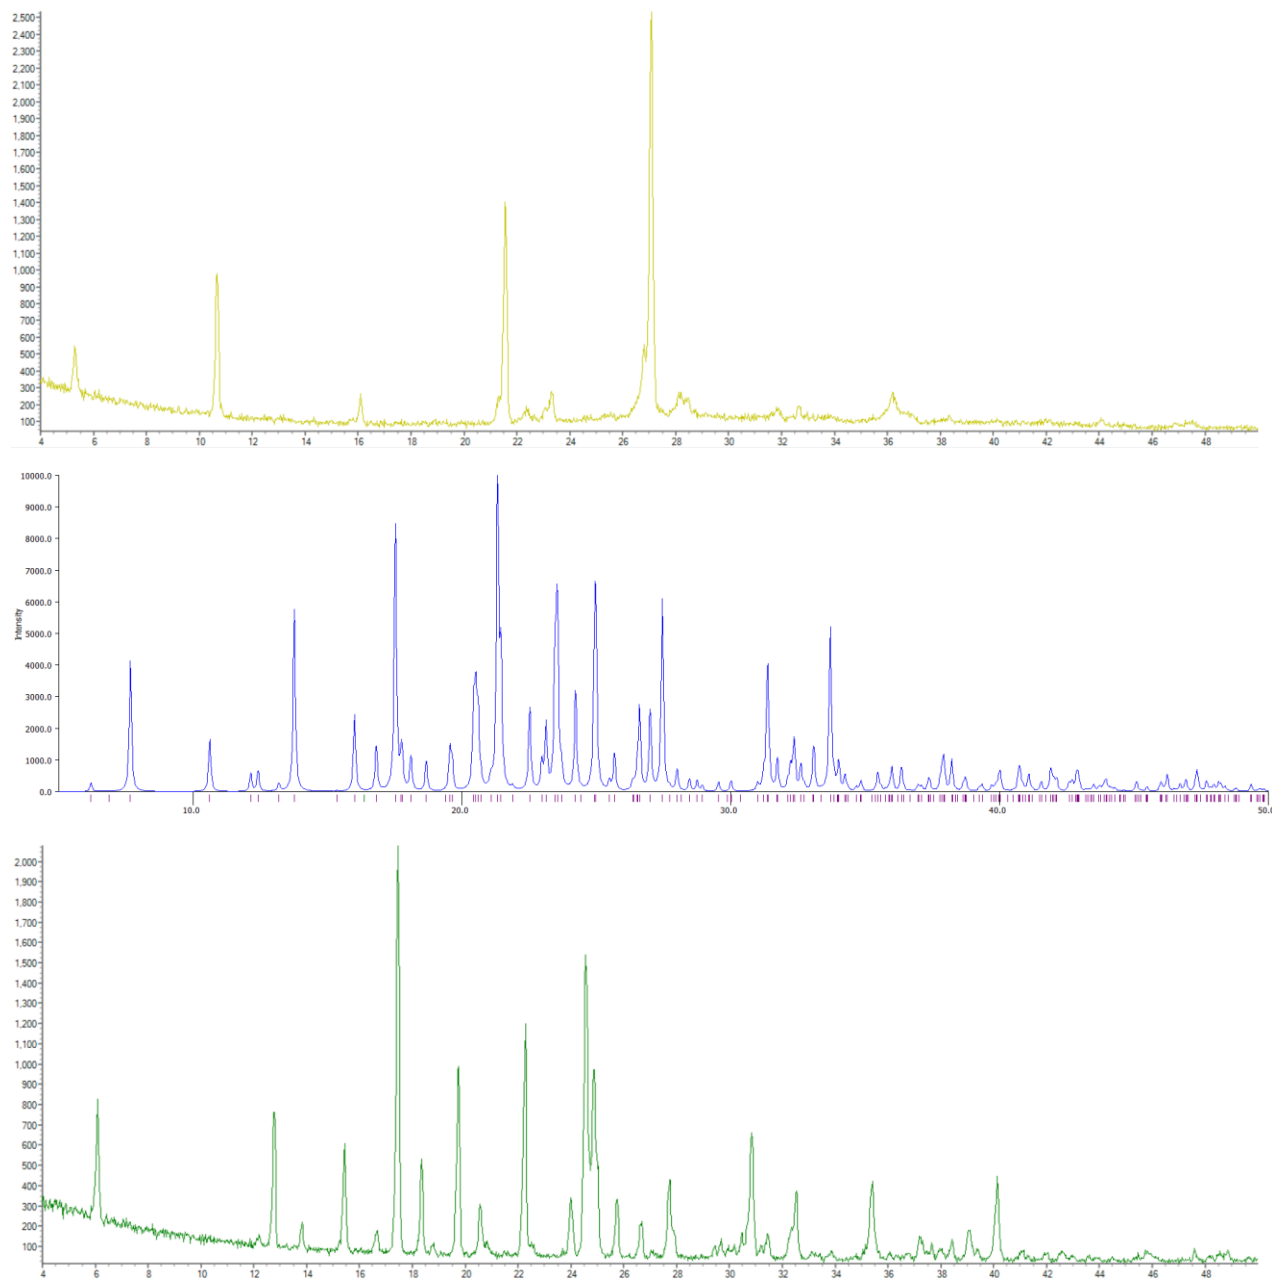


Fig. S8. CI-Phe hydrogel PXRD sample top, with the simulated single crystal pattern middle, and the commercial sample PXRD pattern bottom. The gel sample appears to be showing signs of preferred orientation making it difficult to phase match to the single crystal data.

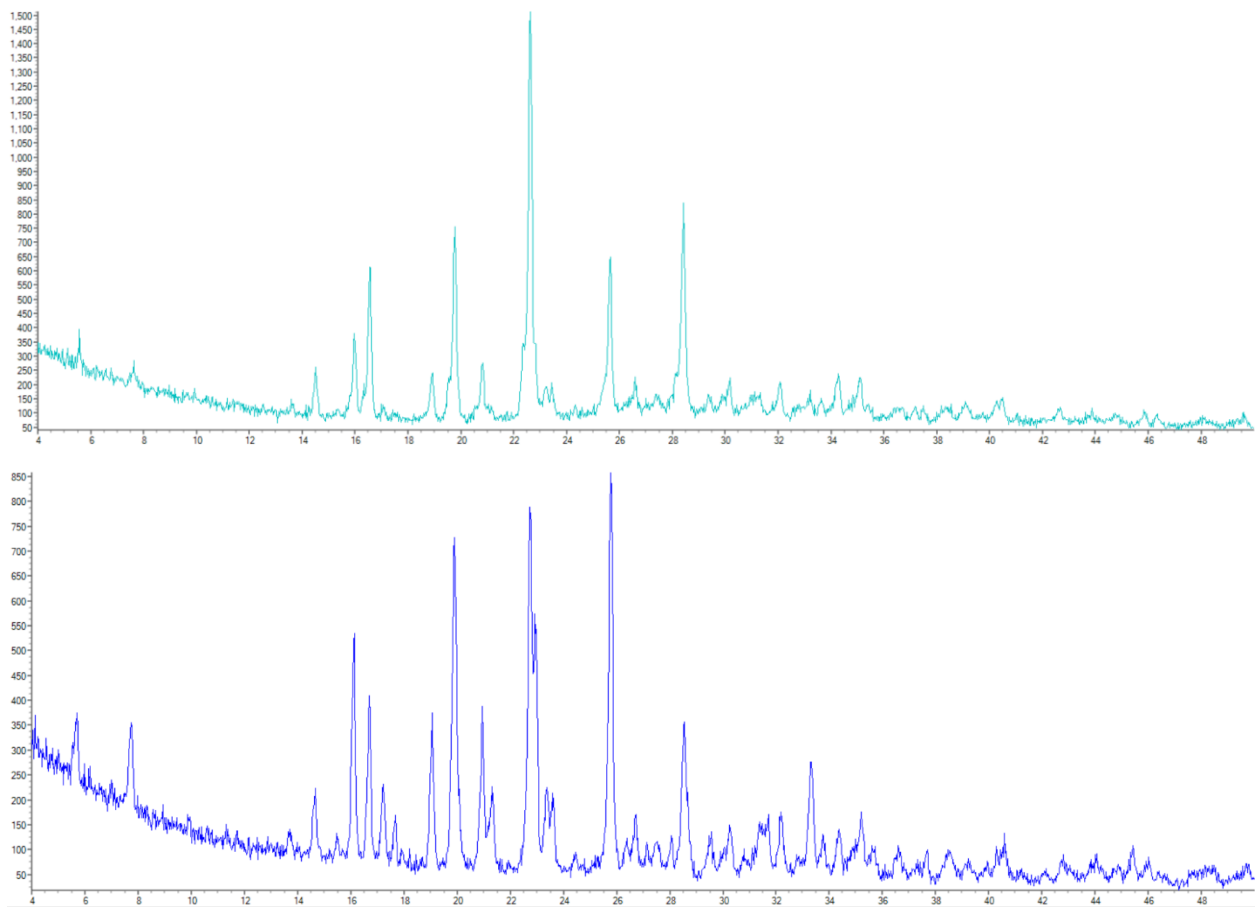


Fig. S9. 2Cl-Phe hydrogel PXRD sample top with commercial product bottom. These two phases appear to be the same.

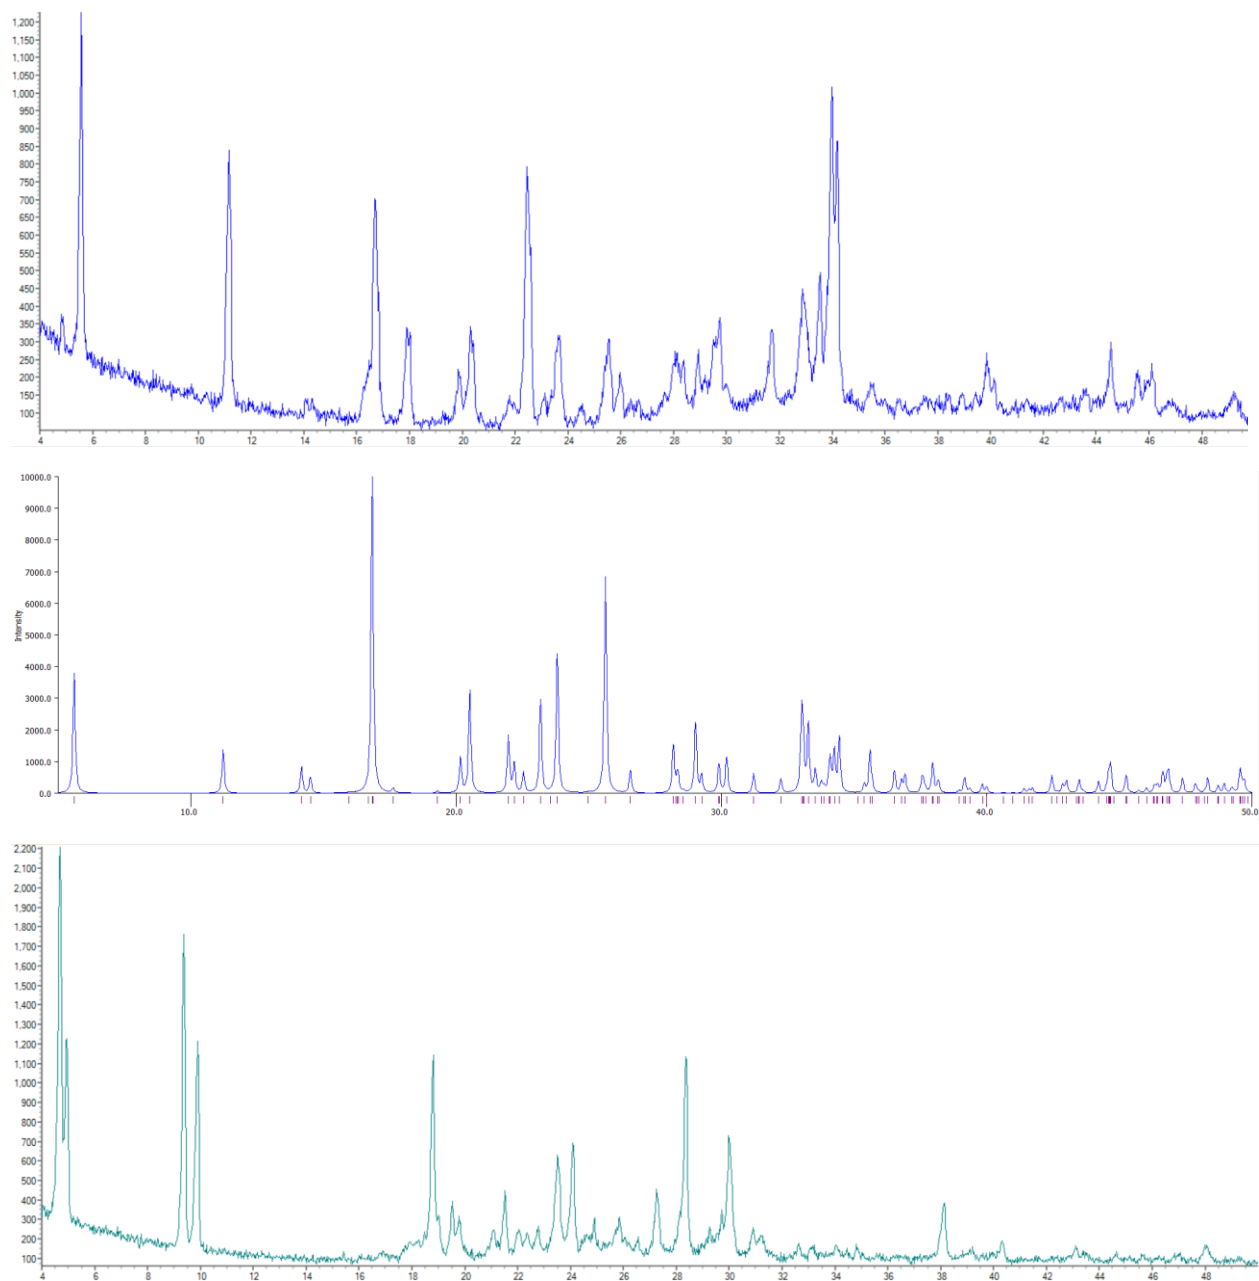


Fig. S10. Br-Phe hydrogel PXRD. Matches the single crystal data, however, there are a number of peaks that do not match. The bottom pattern is the commercial material.

## Single Crystal Diagrams

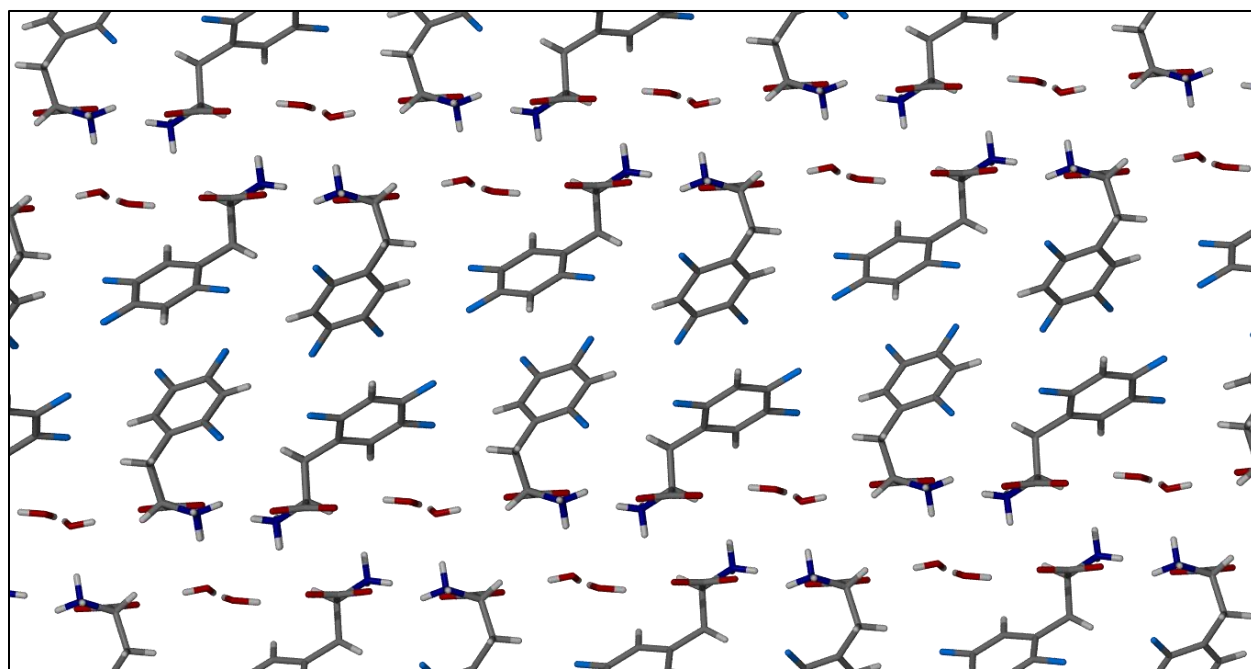


Fig. S11. 2,4,5-trifluorophenylalanine packing.

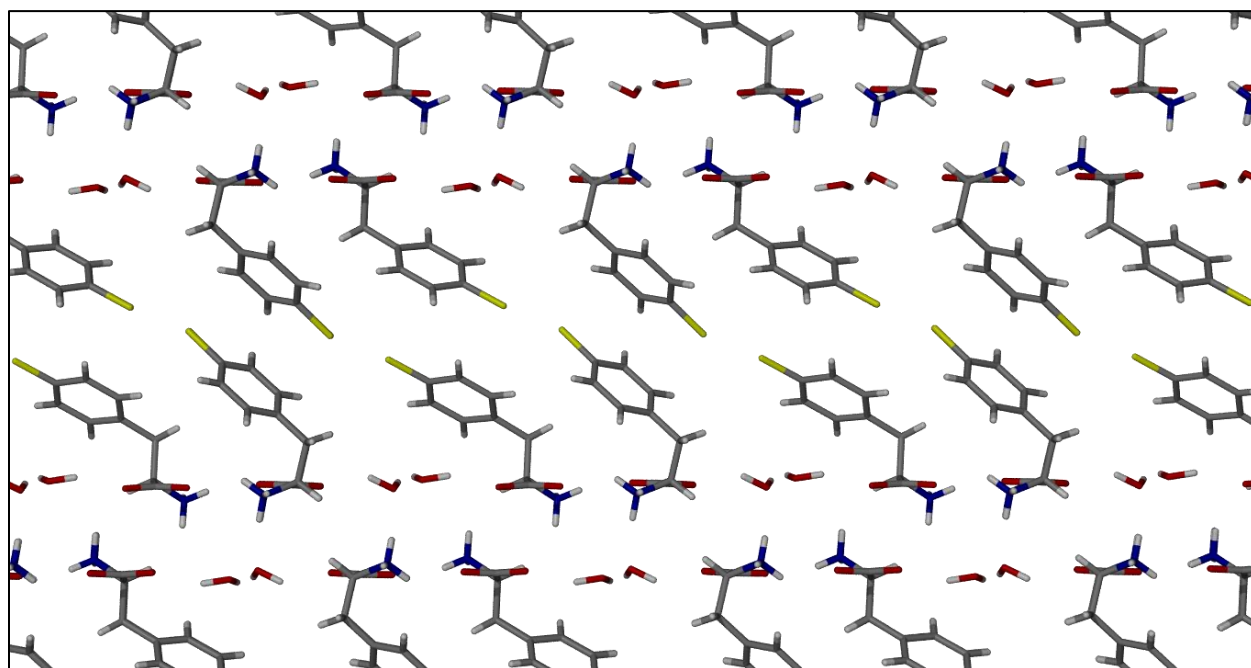


Fig. S12. Cl-Phe packing.

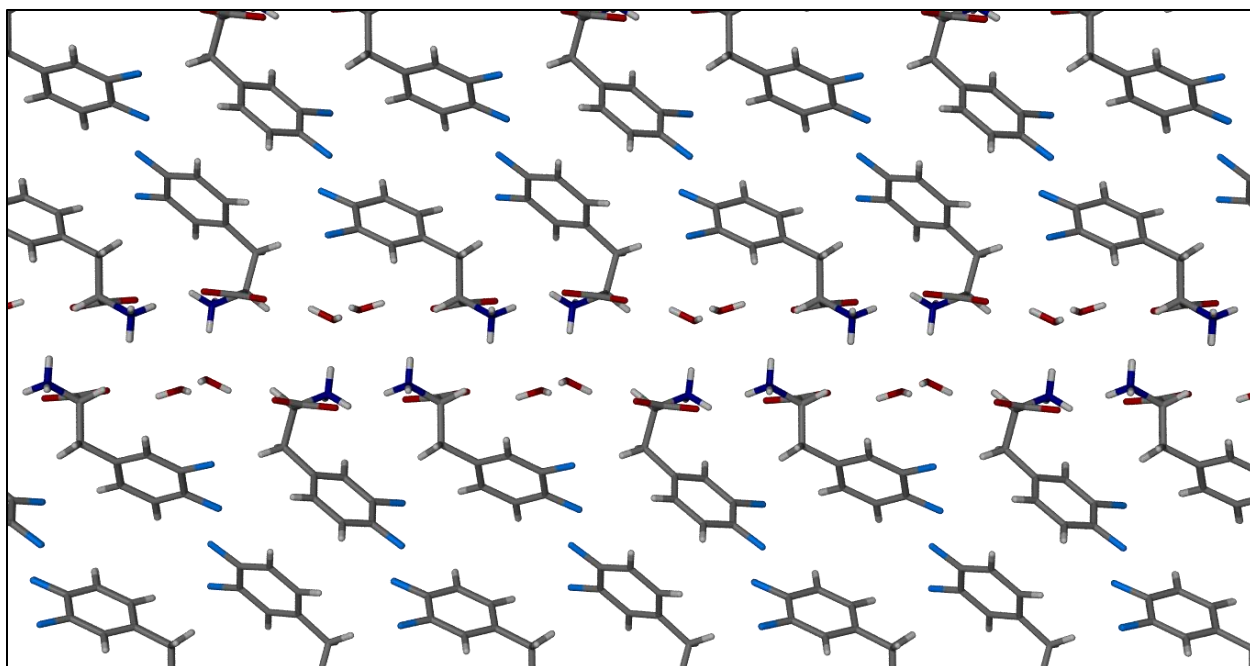


Fig. S13. 2F-Phe packing.

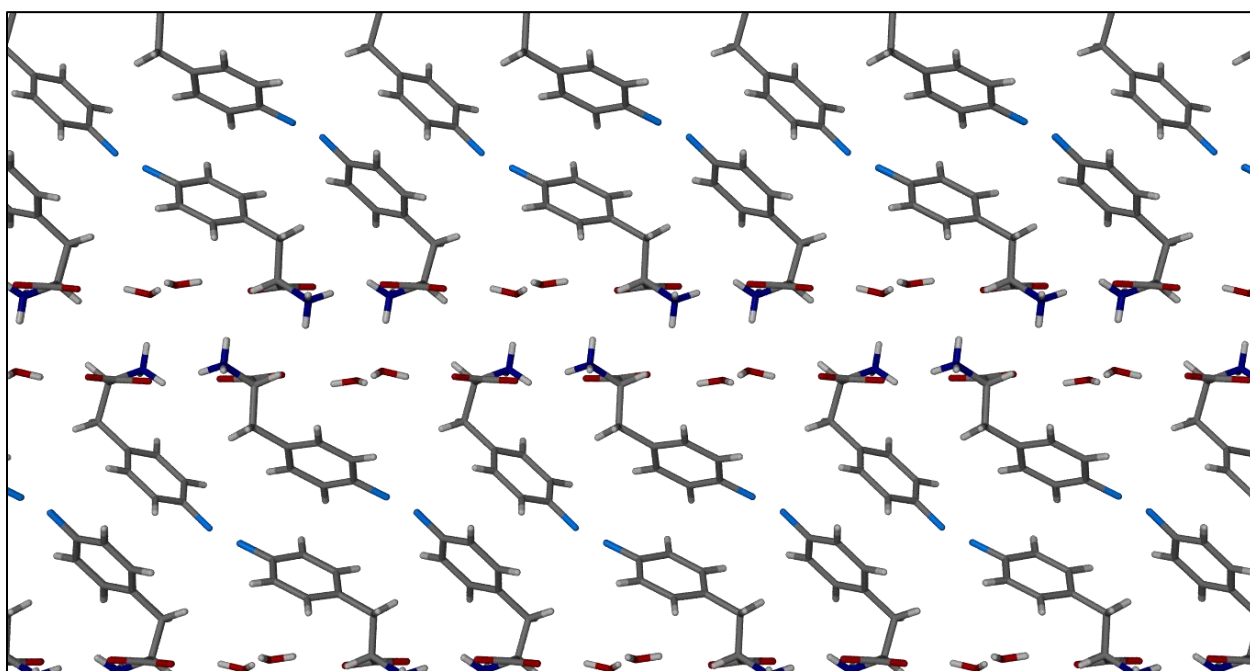


Fig. S14. F-Phe packing

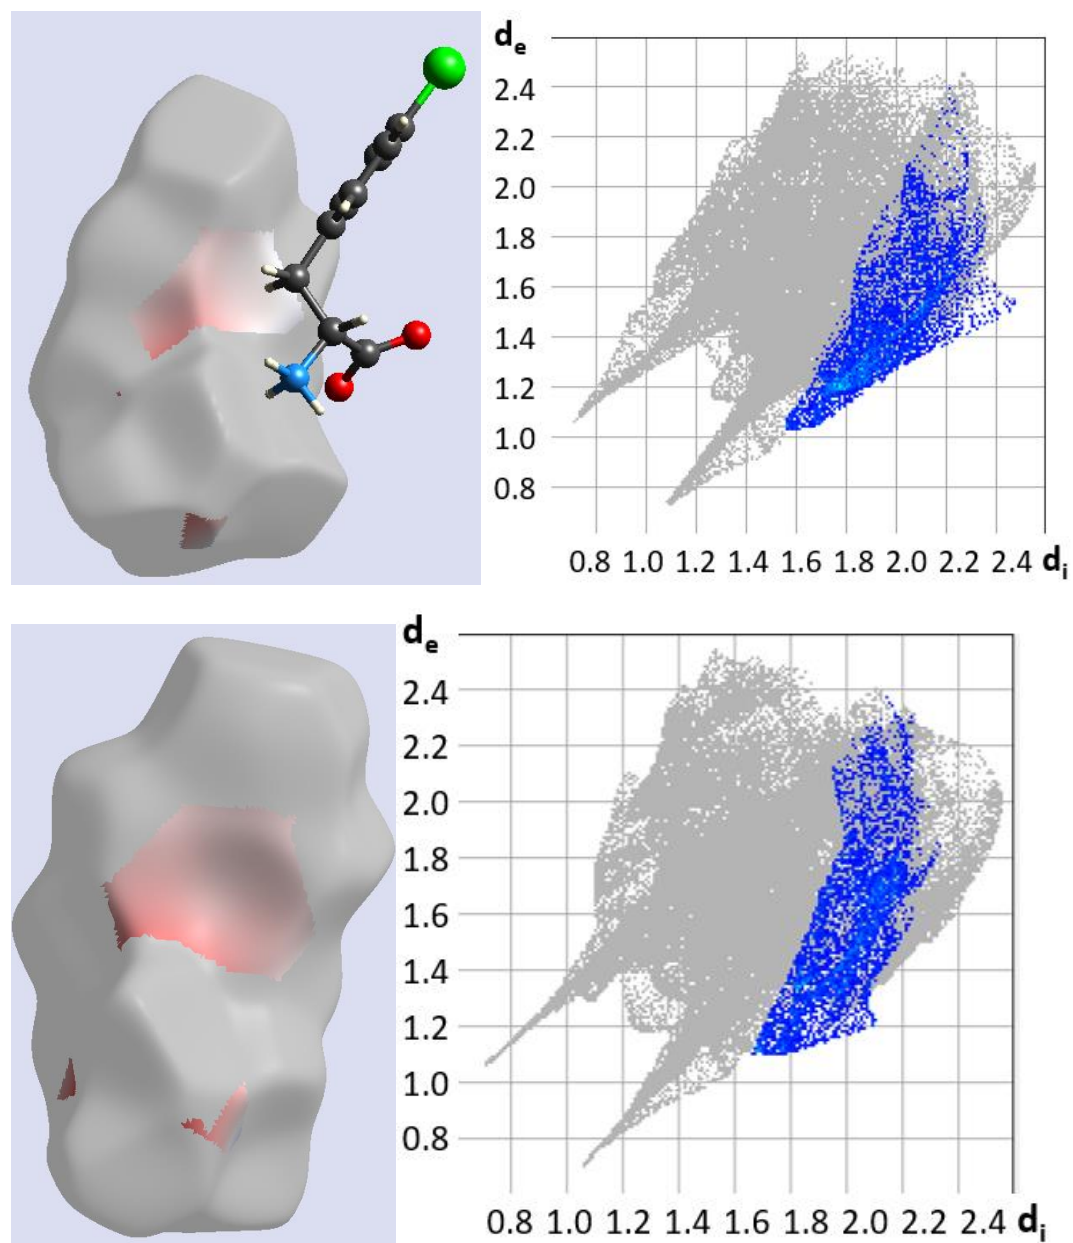


Fig. S15. C-H... $\pi$  interactions/contacts within the Cl-Phe (top) and Br-Phe (bottom) monohydrate structures.

## References

1. a) Y. In, S. Kishima, K. Minoura, T. Nose, Y. Shimohigashi, T. Ishida, *Chem.Pharm.Bull.*, 2003, **51**, 1258; b) Y. Hiyama, J. V. Silverton, D. A. Torchia, J. T. Gerig, S. J. Hammond, *J. Am. Chem. Soc.*, 2986, **108**, 2715.