



Heriot-Watt University  
Research Gateway

## A model of seam pucker and its applications Part I

**Citation for published version:**

Amir, M, Leaf, GAV & Stylios, GK 2020, 'A model of seam pucker and its applications Part I: theoretical', *Journal of The Textile Institute*, vol. 111, no. 1, pp. 64-67. <https://doi.org/10.1080/00405000.2019.1646077>

**Digital Object Identifier (DOI):**

[10.1080/00405000.2019.1646077](https://doi.org/10.1080/00405000.2019.1646077)

**Link:**

[Link to publication record in Heriot-Watt Research Portal](#)

**Document Version:**

Peer reviewed version

**Published In:**

Journal of The Textile Institute

**Publisher Rights Statement:**

This is an Accepted Manuscript of an article published by Taylor & Francis in Journal of the Textile Institute on 5/9/2019, available online: <http://www.tandfonline.com/10.1080/00405000.2019.1646077>

**General rights**

Copyright for the publications made accessible via Heriot-Watt Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

**Take down policy**

Heriot-Watt University has made every reasonable effort to ensure that the content in Heriot-Watt Research Portal complies with UK legislation. If you believe that the public display of this file breaches copyright please contact [open.access@hw.ac.uk](mailto:open.access@hw.ac.uk) providing details, and we will remove access to the work immediately and investigate your claim.

# **A Model of Seam Pucker and Its Applications**

## **Part I: Theoretical**

by

Muhammad Amir<sup>1</sup>, Gerry A.V. Leaf and George K. Stylios\*

Research Institute for Flexible Materials, Heriot Watt University, UK.

\*corresponding author g.stylios@hw.ac.uk

### **Abstract**

This paper considers a simple model of the lock stitch (301) seam, and uses it to derive a measure of the severity of puckering in the seam. The numerical value of the measure depends on the bending properties of the fabrics and thread in the seam, together with the tensions in the threads. How the latter may be estimated is discussed.

### **Keywords**

Seam deformation, pucker severity, garment appearance, garment manufacturing.

### **Introduction**

In garment manufacturing, the fabrics and the threads used to sew pieces of fabric together are highly flexible and easily deformed. If the balance between the various elements of a seam, the threads and the tensions in them, the mechanical properties of the threads and fabrics etc. is not right, the seam will often display an unacceptable deformation known as pucker, i.e. a “waviness” of the seam that is unsightly. Much research has been carried out to try to understand this phenomenon (Dorkin 1961; Zorowski and Patel 1970; O'Dwyer 1975; Amirbayat 1990; Stylios 1990; Amirbayat 1991; Inui, et al. 2001; Jin Lian, et al. 2006; Suzaini and Faizul 2013; Fernando, et al. 2014) but an objective method of calculating the extent of pucker that attempts to balance the above mentioned elements has not emerged.

---

<sup>1</sup> Currently at NED University of Engineering and Technology, Pakistan

The present papers develop such a method by considering a simplified model of the situation when two fabrics are joined by means of a lock stitch (301) seam, one of the most commonly used in the garment industry.

Part I describes the development and theory of the model, while Part II describes its verification and application.

## A Lock Stitch Model

The basic lock stitch (301) is illustrated in Figure 1.

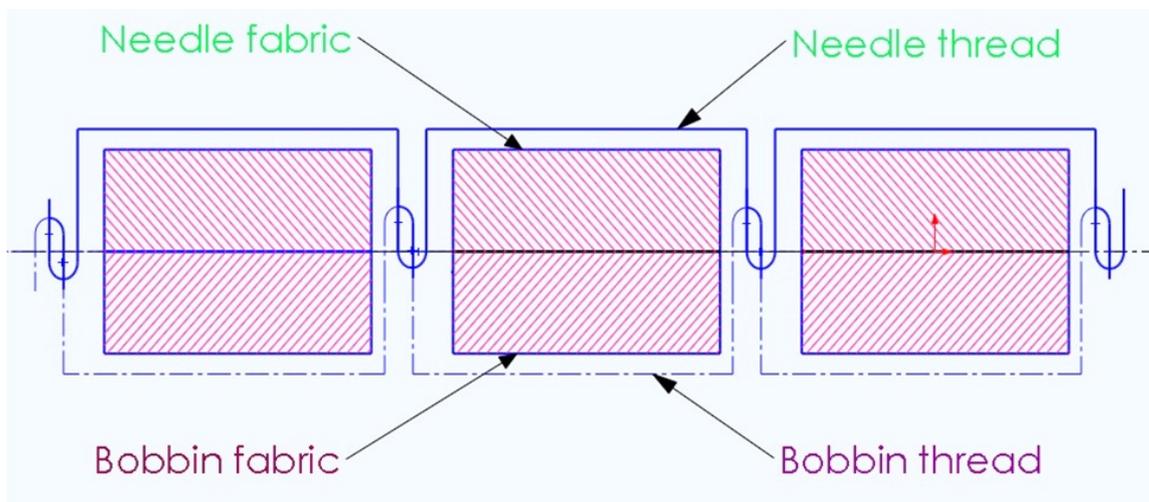


Figure 1. Lock stitch (301) seam profile

The two fabrics are joined by means of two threads, the “needle” thread and the “bobbin” thread, that are locked or interlaced together as shown in the diagram. The two threads generate a normal pressure on the two fabrics, which hold the latter together. A simple idealization of a single stitch of the seam, of length  $l$ , is shown in Figure 2.

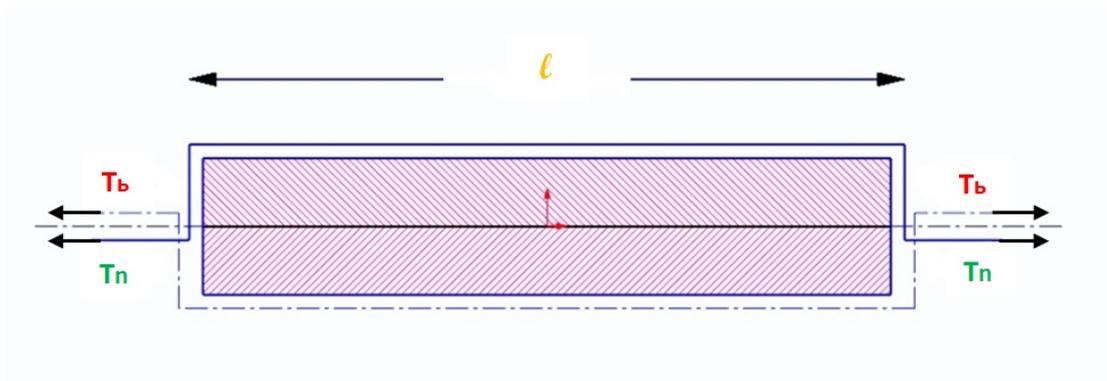


Figure 2. Idealized single stitch

In this diagram  $T_n$  and  $T_b$  are the tensions in the needle and bobbin threads respectively. As they lie in the formed seam. During the stitching operation the threads are subjected to considerable tension, but once the seam has been formed the tensions decrease in the relaxed seam. We shall regard the seam as a beam of width equal to the diameters of the threads, as shown in Figure 3.

If  $B_n$  and  $B_b$  are the bending rigidities per unit width of the two fabrics  $l$  which; for convenience, we shall refer to as the “needle” and “bobbin” fabrics, the bending rigidities of the parts of the fabrics in the beam are  $B'_n = B_n d_n$  and  $B'_b = B_b d_b$ , where  $d_n$  and  $d_b$  are the diameters of the threads.

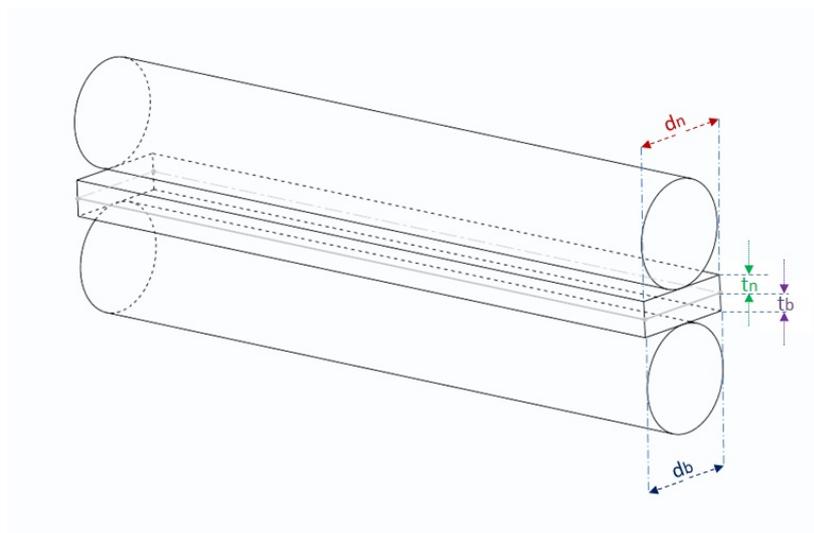


Figure 3 Thickness of the stitched assembly

If  $b_n$  and  $b_b$  are the bending rigidities of the needle and bobbin threads and we assume that all members of the beam in Figure 3 bend independently, the bending rigidity of the “equivalent beam”  $B_e$  is

$$\begin{aligned}
 B_e &= B'_n + B'_b + b_n + b_b \\
 &= B_n d_n + B_b d_b + b_n + b_b \dots \dots \dots (1)
 \end{aligned}$$

When the seam is in equilibrium, this beam will be defined by the pressures generated by the tensions in the threads, as shown in Figure 4.

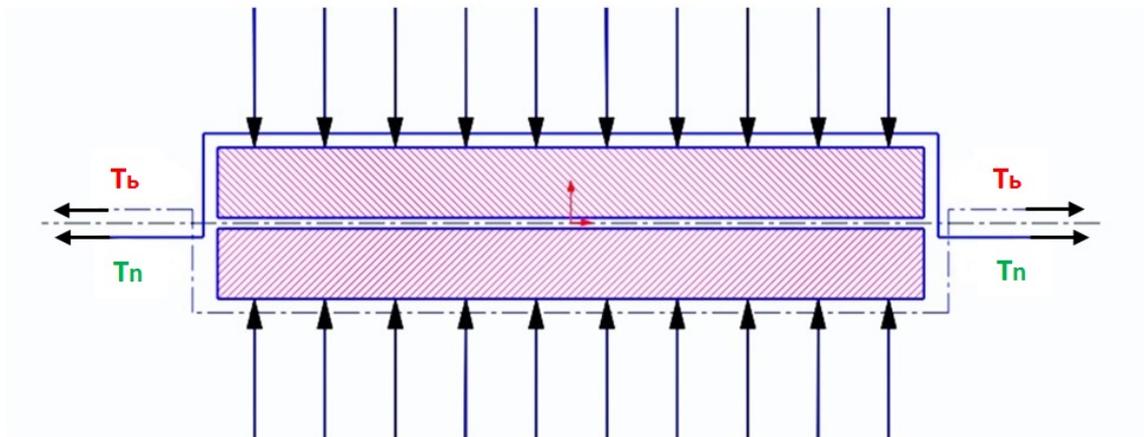


Figure 4 Thread tension produces uniformly distributed pressure

We now assume that the needle thread tension generates a uniformly distributed pressure  $P_n$  per unit length. The total downward force on the beam is therefore  $P_n l$  and this is provided by the vertical tensions  $T_n$ . Thus

$$P_n l = 2T_n ,$$

and similarly

$$P_b l = 2T_b .$$

The resultant uniformly distributed pressure  $P_d$  on the beam is therefore

$$P_d = |P_n - P_b| = \frac{2|T_n - T_b|}{l} \dots \dots \dots (2)$$

This pressure deforms the beam, which we assume to have built-in ends, as shown in Figure 5.




Figure 5 Total stitched fabric thickness

The maximum deflection,  $V_{max}$ , of the beam occurs at its centre and is given by (Seed 2000)

$$V_{max} = \frac{P_d l^4}{384 B_e} = \frac{|T_n - T_b| l^3}{192 B_e} \dots \dots \dots (3)$$

where  $B_e$  is given by equation (1).  $V_{max}$  can be thought of as a measure of the severity of puckering in a seam. However, the same value of  $V_{max}$  would be regarded quite differently, from a pucker point of view, if it referred to a seam involving two relatively thin fabrics as opposed to more robust ones. We therefore suggest a measure called “relative pucker” ( $R_p$ )

which is defined in the following way. The basic idea is to relate  $V_{max}$  to the thickness of the beam assembly. As can be seen from Figure 3 the total thickness of the beam is

$$H = t_n + t_b + d_n + d_b, \dots \dots \dots (4)$$

where  $t_n$  and  $t_b$  are the thicknesses of the needle and bobbin fabrics. After the seam has been formed, Figure 5 shows that the overall thickness of the assembly becomes

$$H_{max} = H + V_{max}$$


The change in thickness due to the seam is  $V_{max}$  and we define relative pucker  $R_p$

$$R_p = \frac{V_{max}}{H} = \frac{V_{max}}{t_n + t_b + d_n + d_b} \dots \dots \dots (5)$$

### The estimation of $|T_n - T_b|$

A prominent feature of equation (3) is the appearance of the difference  $|T_n - T_b|$  in the thread tensions as they lie in the relaxed seam. Such tensions would be extremely difficult to measure directly without introducing considerable errors of measurement. Therefore a different approach has been employed to estimate the magnitude of  $|T_n - T_b|$ .

Suppose a length of the joined fabrics, including the seam, is extended parallel to the seam, and let the width of the specimen be  $w$ . Consider a single stitch, as shown in Figure 6, extended from length  $l$  to length  $l(1 + \epsilon)$ .

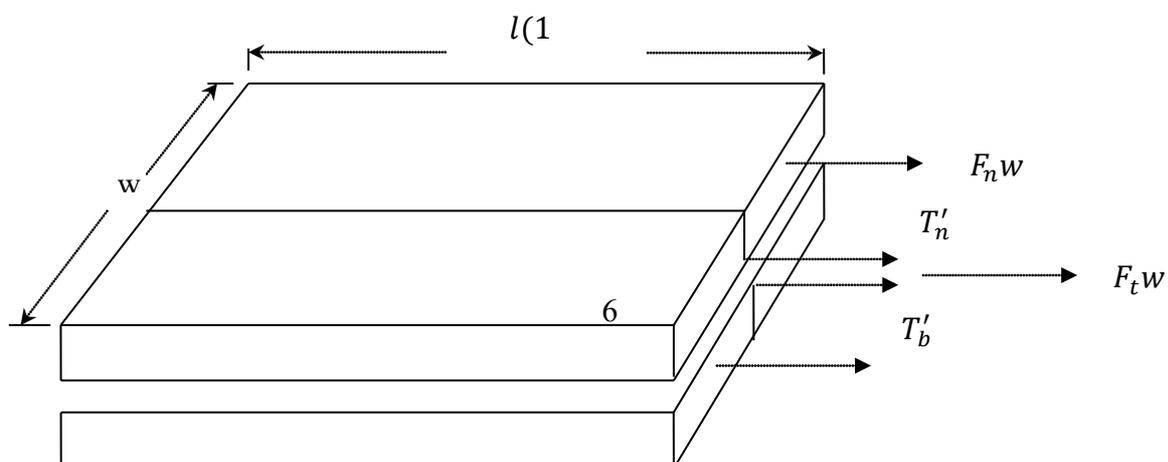

$$F_b w$$

Figure 6 Force components on an individual stitch

The total force  $F_t w$  needed to produce an extension  $\epsilon$  is made up of several components, as shown in Figure 6. They are

- a) Forces  $F_n w$  and  $F_b w$  needed to extend the two fabrics;
- b) the tensions  $T'_n$  and  $T'_b$  in the extended needle and bobbin threads.

Thus we have

$$F_t w = F_n w + F_b w + T'_n + T'_b \dots \dots \dots (6)$$

Suppose the fabrics obey Hooke's law for small extensions, i.e.

$$F_n = E_n \epsilon, \quad F_b = E_b \epsilon,$$

where  $E_n$  and  $E_b$  are the Young's moduli of the fabrics.

The thread tensions  $T'_n$  and  $T'_b$  in the extended seam may be found as follows. We assume that if a tension  $T$  is applied to a thread and produces an extension  $\epsilon_y$  then

$$T = e \epsilon \epsilon_y$$

where  $e$  is the thread's Young's modulus. After the seam is formed the tensions in the yarns are  $T_n$  and  $T_b$ ; thus the yarns are already stretched and their natural length is smaller than  $l$ . In fact, if  $l_0$  is the natural length we have, for the needle thread,

$$T_n = e_n \epsilon_y = e_n (l - l_{0n}) / l_{0n},$$

leading to

$$l_{0n} = \frac{e_n l}{T_n + e_n} \dots \dots \dots (7)$$

Similarly

$$l_{0b} = \frac{e_b l}{T_b + e_b} \dots \dots \dots (8)$$

When the seam is extended and the needle thread tension increases to  $T'_n$  we find that

$$T'_n = e_n \left\{ \frac{l(1 + \varepsilon) - l_{0n}}{l_{0n}} \right\}$$

which leads to

$$T'_n = (1 + \varepsilon)(T_n + e_n) - e_n$$

after using equation (7).

Similarly,

$$T'_b = (1 + \varepsilon)(T_b + e_b) - e_b$$

Hence in equation (6) we get

$$\begin{aligned} F_t w &= (F_n + F_b)w + (1 + \varepsilon)(T_n + e_n) - e_n + (1 + \varepsilon)(T_b + e_b) - e_b \\ &= (E_n + E_b)w\varepsilon + (1 + \varepsilon)(T_n + T_b) + \varepsilon(e_n + e_b) \dots \dots \dots (9) \end{aligned}$$

This equation would allow the sum of the tensions ( $T_n + T_b$ ) to be estimated. However, we require the size of their difference ( $T_n - T_b$ ) to be entered in equation (3) to calculate  $V_{max}$ . To estimate this difference, consider the following.

Suppose a fairly long piece of seam of length  $L = nl$  is clamped between the jaws of a tensile tester, and suppose also that the bobbin thread of a stitch close to the clamps is cut. The bobbin threads in the main part of the seam are still intact and because of friction, will play some role in opposing the seam extension. However, the tensile tester will not measure “see” the bobbin thread tension and equation (9) would apply with  $T_b = 0$ . The tension  $T_n$



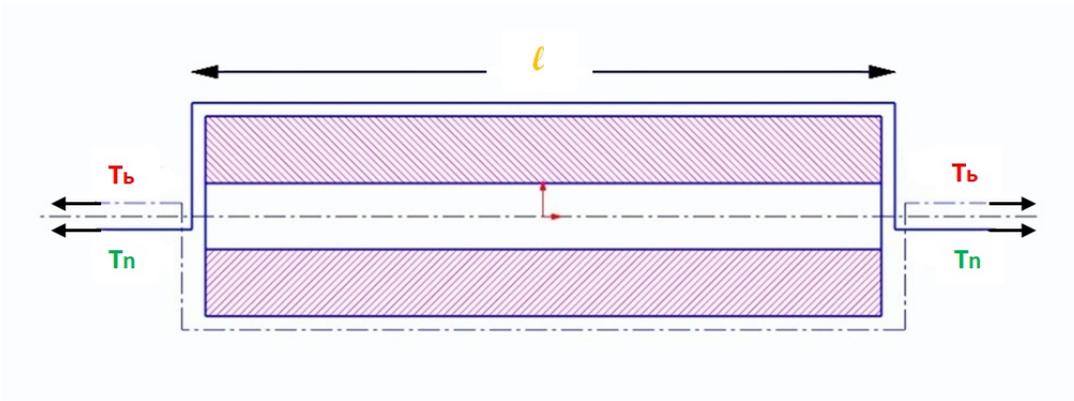


Figure 7 Model of the equivalent beam with stiffener

If the bending rigidity of the stiffener is  $B_s$  per unit width, then, if  $\bar{d} = \frac{1}{2}(d_n + d_b)$  is the mean thickness of the equivalent beam, we deduce that the contribution of the stiffener to the bending rigidity of the beam is  $B'_s = B_s \bar{d}$ . The total rigidity of the beam becomes

$$\begin{aligned}
 B_{es} &= B_e + B'_s = B_e + B_s \bar{d} \\
 &= B_n d_n + B_b d_b + b_n + b_b + B_s \bar{d} \dots \dots \dots (11)
 \end{aligned}$$

which is obviously greater than the bending rigidity of the unstiffened beam given by equation (1). Hence the value of  $V_{max}$  is reduced and therefore the severity of the puckering. The advantage of this approach is that in a practical case of puckering the properties of the stiffener needed to reduce the severity of puckering to an acceptable level can be calculated.

## Conclusion

This paper has presented a simplified model of a lock stitch seam. The model was then used to derive a proposed measure of the severity of puckering in the seam. This measure depends on the bending properties of the fabrics and threads composing the seam and on the difference in the tensions in the needle and bobbin threads as they lie in the seam. A practical method of estimating this difference has been suggested. The experimental verification of the measure and its application are dealt with in Part II.

## References

- Amirbayat, J. (1990). "An Energy Approach to the Instability Problem of Overfeed Seams: Part 1: Theoretical Analysis " International Journal of Clothing Science and Technology **2**(1): 21-25.
- Amirbayat, J. (1991). "Profile of Lockstitch Seams. A Theoretical Study." Textile Research Journal **61**(2): 119-122.
- Dorkin, C. M. C. (1961). "Seam Pucker: Its Cause and Prevention" , Clothing Institute Technological Report No.21.
- Fernando, S., Jayawardena T, et al. (2014). "Measurement of Seam Puckering and Influence of its Causes." Measurement **4**(04).
- Stylios, G and Lloyd D.W. (1990). "Prediction of Seam Pucker in Garments By Measuring Fabric Mechanical Properties and Geometric Relationship." International journal of Clothing and Science and Technology **2**(1): 6-15.
- Stylios, G. K. (2013). The appearance of seams in non-iron shirts. In I. Jones, & G. K. Stylios (Eds.), *Joining Textiles: Principles and Applications* (No. 110 ed., pp. 467-477). (Woodhead Publishing Series in Textiles No. 110). UK: Woodhead Publishing Ltd.. DOI: [10.1533/9780857093967.4.467](https://doi.org/10.1533/9780857093967.4.467)
- Inui, S., Okabe H, et al. (2001). "Simulation of Seam Pucker on Two Strips of Fabric Sewn Together." International Journal of Clothing Science and Technology **13**(1): 53-64.
- Jin Lian, H., Ma L, et al. (2006). "Modelling Multi-layer Seam Puckering." Textile Research Journal **76**(9): 665-673.
- Seed, G. M. (2000). *Strength of Materials: An Undergraduate Text*, Saxe-Coburg Publications.
- Suzaini, A. G. and Faizul Y. (2013). Seam Puckering: Analysis and Modeling with Structural Equation Modeling. Advanced Materials Research, Trans Tech Publ.
- O'Dwyer, U and Munden D. L. (1975). "A Study of The Lock Stitch Seam " Clothing Research Journal **3**(1): 1-40.
- Zorowski, C. F. and Patel G. C. (1970). "Seam Puckering as a Mechanical Instability Phenomenon." Journal of Manufacturing Science and Engineering **92**(1): 17-22.