



Heriot-Watt University
Research Gateway

Direct laser-writing of optical micro-structures for robust traceability marking of metal components

Citation for published version:

Włodarczyk, KL, Ardron, M, Weston, N, Kidd, M & Hand, DP 2014, 'Direct laser-writing of optical micro-structures for robust traceability marking of metal components', Paper presented at 15th International Symposium on Laser Precision Microfabrication 2014, Vilnius, Lithuania, 17/06/14 - 20/06/14.

Link:

[Link to publication record in Heriot-Watt Research Portal](#)

Document Version:

Peer reviewed version

General rights

Copyright for the publications made accessible via Heriot-Watt Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

Heriot-Watt University has made every reasonable effort to ensure that the content in Heriot-Watt Research Portal complies with UK legislation. If you believe that the public display of this file breaches copyright please contact open.access@hw.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.

Direct laser-writing of optical micro-structures for robust traceability marking of metal components

K. L. Wlodarczyk¹, M. Ardron^{1,2}, M. Kidd², N. J. Weston², D. P. Hand¹

1- Institute of Photonics and Quantum Sciences, School of Engineering and Physical Sciences, Heriot-Watt University, Edinburgh, EH14 4AS, United Kingdom

2- Renishaw plc, Research Park North, Riccarton, Edinburgh, EH14 4AP, United Kingdom

Main author email address: K.L.Wlodarczyk@hw.ac.uk

Full traceability of components is essential in medical and aerospace sectors. Common approaches to unique marking include etching of serial numbers and bar codes or the use of a polymer holographic sticker which is typically produced by a mechanical embossing process. The hologram is robust to local damage, its information being distributed over a wide area, where serial numbers and bar codes are not. The serious disadvantage of such holograms, however, is that they are not embedded into the metal surface, but are rather attached as an adhesive tape, and therefore are vulnerable to tampering and present biocompatibility problems for implants.

This paper presents a laser-based process for the direct embossing of phase holograms on the surface of metal parts (e.g. 304-grade stainless steel). In order to achieve an optical surface finish, we use a nanosecond laser operating at a 355 nm wavelength. This approach allows the metal surface to be structured (either by melting or the combination of melting and evaporation) with the required sub-micron depth control. As reported elsewhere [1], surface structuring by a melt-only process is possible because UV nanosecond laser pulses produce a very shallow melt pool with a transverse thermal gradient since the laser beam is more intense in the centre. This gives rise to a surface tension gradient across the surface of the melt pool which causes a flow of the molten material. This type of flow is known as the Marangoni effect [2].

Figure 1 (a) shows a sample of 304-grade stainless steel with a laser-written micro-structure containing coded information (the small square in the centre). The micro-structure represents a binary (two-level) diffractive optical element (DOE) whose design was performed using the Iterative Fourier Transform Algorithm [3]. The DOE was generated by a 10 μm diameter focused laser beam with pulse energy of 2.5 μJ . At this pulse energy, each pixel of the DOE is an optically-smooth crater with a peak-to-valley depth of approximately 300 nm. The close-up (top) view of the DOE is shown in Figure 1 (b). When the DOE is illuminated with a laser source (e.g. a He-Ne laser), it produces a clear diffraction image with the undiffracted (zero-order) laser beam in the centre, as can be seen in Figure 1 (c).

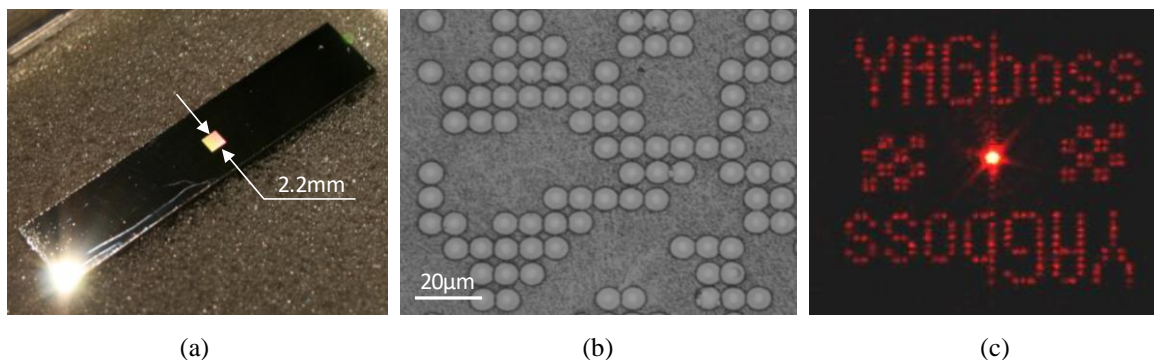


Figure 1 (a) 304-grade stainless steel with a laser-written DOE, (b) optical microscope image of the DOE, and (c) image generated by the DOE when illuminated by a He-Ne laser beam.

A detailed discussion of the laser-based process for the generation of traceability markings (DOEs) on metal surfaces will be presented, and more complex microstructures than that shown in Figure 1 will be demonstrated. Results with different metals (e.g. nickel) will also be presented.

- [1] N.J. Weston, D.P. Hand, S. Giet, and M. Ardron, "A method of forming an optical device," Patent No.: WO/2012/038707 (2012).
- [2] T. Hibiya and S. Ozawa, "Marangoni flow and surface tension of high temperature melts", in *High-temperature measurements of materials*, H. Fukuyama and Y. Waseda, eds. (Springer Berlin Heidelberg), Chapter 3, pp. 39-57, (2009).
- [3] F. Wyrowski and O. Bryngdahl, "Iterative Fourier-transform algorithm applied to computer holography," *J. Opt. Soc. Am. A* 5, 1058-1065 (1988).